

OIL ANALYSIS REPORT

Sample Rating Trend





DIAGNOSIS

Recommendation

Resample at the next service interval to monitor. Please specify the component make and model with your next sample. Please specify the brand, type, and viscosity of the oil on your next sample.

Wear


All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.







SAMPLE INFORM	IATION	method	limit/base	current	history1	history2
Sample Number		Client Info		WC0860358	WC0844992	WC0827068
Sample Date		Client Info		08 Nov 2023	05 Sep 2023	27 Jul 2023
Machine Age	mls	Client Info		214597	208957	203357
Oil Age	mls	Client Info		0	0	0
Oil Changed		Client Info		Changed	Changed	N/A
Sample Status				NORMAL	NORMAL	NORMAL
CONTAMINATIO	N	method	limit/base	current	history1	history2
Fuel		WC Method	>5	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method	, 0.1	NEG	NEG	NEG
-			limit/booo	-		
WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>100	11	7	8
Chromium	ppm	ASTM D5185m		<1	0	<1
Nickel	ppm	ASTM D5185m	>4	<1	0	0
Titanium	ppm	ASTM D5185m		<1	<1	0
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m		2	<1	2
Lead	ppm	ASTM D5185m	>40	0	<1	0
Copper	ppm	ASTM D5185m		<1	3	2
Tin	ppm	ASTM D5185m	>15	<1	0	0
Vanadium	ppm	ASTM D5185m		<1	0	0
Cadmium	ppm	ASTM D5185m		0	0	0
ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	250	121	19	16
Barium	ppm	ASTM D5185m	10	0	0	2
Molybdenum	ppm	ASTM D5185m	100	76	77	82
Manganese	ppm	ASTM D5185m		<1	0	<1
Magnesium	ppm	ASTM D5185m	450	324	261	291
Calcium	ppm	ASTM D5185m	3000	1363	2019	2071
Phosphorus	ppm	ASTM D5185m	1150	878	1059	1078
Zinc	ppm	ASTM D5185m	1350	1122	1352	1338
Sulfur	ppm	ASTM D5185m	4250	2838	3634	4196
CONTAMINANTS	;	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>25	13	7	7
Sodium	ppm	ASTM D5185m	>158	4	7	9
Potassium	ppm	ASTM D5185m	>20	1	1	<1
INFRA-RED		method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844	>3	0.4	0.3	0.3
Nitration	Abs/cm	*ASTM D7624	>20	9.1	10.3	10.5
Sulfation	Abs/.1mm	*ASTM D7415	>30	23.5	22.0	22.0
FLUID DEGRADA	TION	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414	>25	20.7	18.8	19.1
Base Number (BN)	mg KOH/g	ASTM D2896		4.4	5.9	5.9
· · · /	0 0					




OIL ANALYSIS REPORT

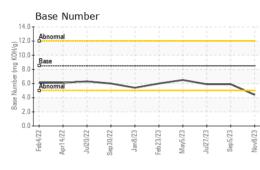



VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG	NEG
FLUID PROPER	TIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	14.4	13.5	14.1	13.8
GRAPHS						

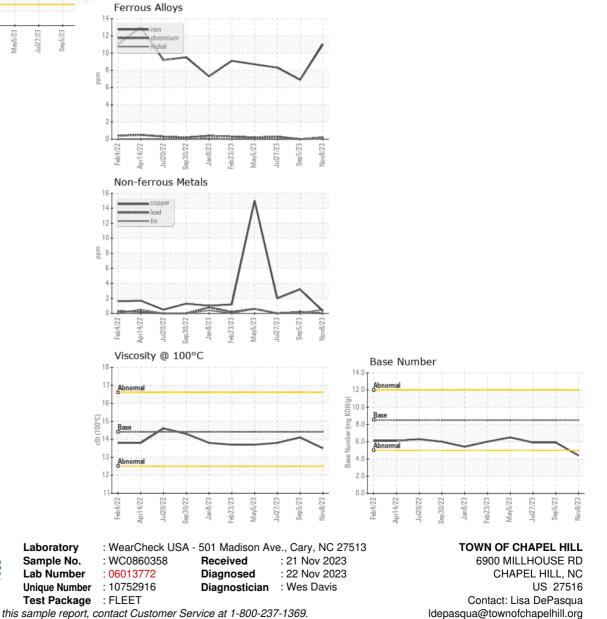



To discuss this sample report, contact Customer Service at 1-800-237-1369. Ide * - Denotes test methods that are outside of the ISO 17025 scope of accreditation. Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

Certificate L2367

F:

T: (919)696-4941