

Sample Rating Trend

NORMAL



Machine Id **F-04** Component **Wind Turbine Gearbox** Fluid **ROYAL PURPLE SYNFILM GT 320 (65 GAL)**

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil. The amount and size of particulates present in the system are acceptable.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

| SAMPLE INFORM | ATION | method | limit/base | current | history1 | history2 |
|-----------------|-------|--------------|------------|-------------|-------------|-------------|
| Sample Number | | Client Info | | MHI021628 | MHI019452 | MHI000002 |
| Sample Date | | Client Info | | 07 Jun 2023 | 12 Jul 2021 | 24 Aug 2020 |
| Machine Age | hrs | Client Info | | 0 | 0 | 0 |
| Oil Age | hrs | Client Info | | 0 | 0 | 0 |
| Oil Changed | | Client Info | | N/A | N/A | Not Changd |
| Sample Status | | | | NORMAL | NORMAL | SEVERE |
| WEAR METALS | | method | limit/base | current | history1 | history2 |
| PQ | | ASTM D8184 | >200 | 13 | 20 | |
| Iron | ppm | ASTM D5185m | >200 | 10 | 6 | |
| Chromium | ppm | ASTM D5185m | >3 | <1 | 0 | |
| Nickel | ppm | ASTM D5185m | >3 | 0 | 0 | |
| Titanium | ppm | ASTM D5185m | >10 | <1 | 0 | |
| Silver | ppm | ASTM D5185m | | 0 | 0 | |
| Aluminum | ppm | ASTM D5185m | >30 | 2 | 0 | |
| Lead | ppm | ASTM D5185m | >15 | 0 | 0 | |
| Copper | ppm | ASTM D5185m | >75 | 5 | 3 | |
| Tin | ppm | ASTM D5185m | >10 | 0 | 0 | |
| Antimony | ppm | ASTM D5185m | >5 | | <1 | |
| Vanadium | ppm | ASTM D5185m | | 0 | 0 | |
| Cadmium | ppm | ASTM D5185m | | 0 | 0 | |
| ADDITIVES | | method | limit/base | current | history1 | history2 |
| Boron | ppm | ASTM D5185m | | 0 | <1 | |
| Barium | ppm | ASTM D5185m | | 0 | 0 | |
| Molybdenum | ppm | ASTM D5185m | | <1 | <1 | |
| Manganese | ppm | ASTM D5185m | | 0 | <1 | |
| Magnesium | ppm | ASTM D5185m | 90 | 24 | 40 | |
| Calcium | ppm | ASTM D5185m | 50 | <1 | 0 | |
| Phosphorus | ppm | ASTM D5185m | | 0 | 33 | |
| Zinc | | ASTM D5185m | | 0 | 0 | |
| Sulfur | ppm | ASTM D5185m | | 20882 | 15867 | |
| | ppm | | | | | |
| CONTAMINANTS | | method | limit/base | current | history1 | history2 |
| Silicon | ppm | ASTM D5185m | >+30 | 5 | 4 | |
| Sodium | ppm | ASTM D5185m | | 0 | 0 | |
| Potassium | ppm | ASTM D5185m | >20 | 1 | 0 | |
| Water | % | ASTM D6304 | >0.1 | 0.009 | 0.006 | |
| ppm Water | ppm | ASTM D6304 | >1000 | 98 | 67.5 | |
| FLUID CLEANLINI | ESS | method | limit/base | current | history1 | history2 |
| Particles >4µm | | ASTM D7647 | | 690 | 21099 | |
| Particles >6µm | | ASTM D7647 | >5000 | 204 | 3385 | |
| Particles >14µm | | ASTM D7647 | >640 | 18 | 159 | |
| Particles >21µm | | ASTM D7647 | >160 | 3 | 35 | |
| Particles >38µm | | ASTM D7647 | >40 | 0 | 4 | |
| Particles >71µm | | ASTM D7647 | >10 | 0 | 1 | |
| Oil Cleanliness | | ISO 4406 (c) | >/19/16 | 17/15/11 | 22/19/14 | |
| | | | | | | |



Water (KF)

Feb15/12

Feb15/12

Particle Trend

25 20

) sapticles (10k 1av8/19

12000 10000 - See 8000 (udd) 6000 2000 - Ab

0ct18/


OIL ANALYSIS REPORT


17/23

Color

Bottom

| FLUID DEGRADA | TION | method | limit/base | current | history1 | history2 |
|------------------|----------|------------|------------|---------|----------|----------|
| Acid Number (AN) | mg KOH/g | ASTM D8045 | 0.25 | 0.41 | 0.43 | |
| VISUAL | | method | limit/base | current | history1 | history2 |
| White Metal | scalar | *Visual | NONE | NONE | LIGHT | VLITE |
| Yellow Metal | scalar | *Visual | NONE | NONE | NONE | NONE |
| Precipitate | scalar | *Visual | NONE | NONE | NONE | NONE |
| Silt | scalar | *Visual | NONE | NONE | NONE | NONE |
| Debris | scalar | *Visual | NONE | LIGHT | VLITE | NONE |
| Sand/Dirt | scalar | *Visual | NONE | NONE | NONE | VLITE |
| Appearance | scalar | *Visual | NORML | NORML | NORML | NORML |
| Odor | scalar | *Visual | NORML | NORML | NORML | NORML |
| Emulsified Water | scalar | *Visual | >0.1 | NEG | NEG | |
| Free Water | scalar | *Visual | | NEG | NEG | |
| FLUID PROPERT | IES | method | limit/base | current | history1 | history2 |
| Visc @ 40°C | cSt | ASTM D445 | 320 | 325 | 327.3 | |
| SAMPLE IMAGES | | method | limit/base | current | history1 | history2 |



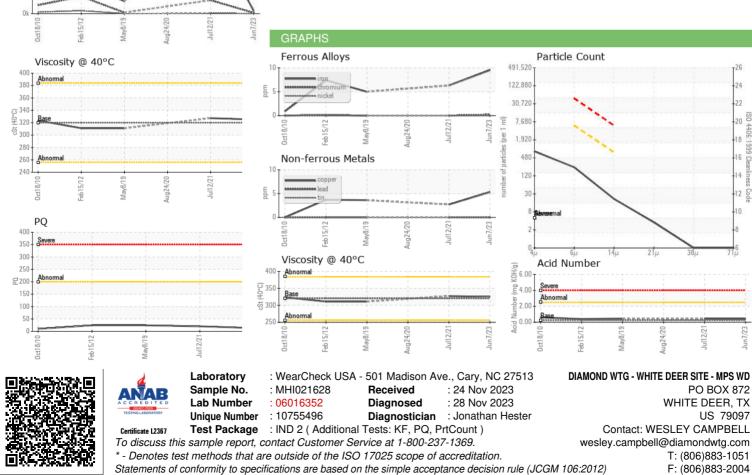

Contact/Location: WESLEY CAMPBELL - MITWHI