OIL ANALYSIS REPORT

Sample Rating Trend

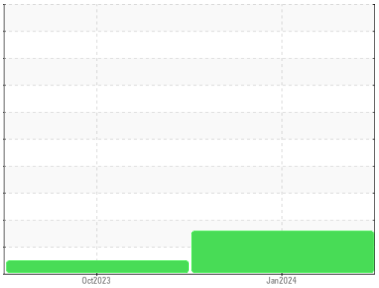

WEAR

Machine Id
JOHN DEERE 624 P 1DW624PACPLX19407
Component
Front Axle
Fluid
JOHN DEERE HY-GARD HYD/TRANS (--- GAL)

DIAGNOSIS

▲ Recommendation
No corrective action is recommended at this time. Resample at the next service interval to monitor.

▲ Wear
Bearing and/or bushing wear is indicated.

Contamination
There is no indication of any contamination in the oil.

Fluid Condition
The condition of the oil is acceptable for the time in service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number		Client Info		**JR0200283**	JR0179130	---
Sample Date		Client Info		**04 Jan 2024**	19 Oct 2023	---
Machine Age	hrs	Client Info		**947**	480	---
Oil Age	hrs	Client Info		**0**	480	---
Oil Changed		Client Info		**Not Changd**	N/A	---
Sample Status				**ABNORMAL**	NORMAL	---

CONTAMINATION		method	limit/base	current	history1	history2
Water		WC Method	>0.1	**NEG**	NEG	---

WEAR METALS		method	limit/base	current	history1	history2
PQ		ASTM D8184		**24**	16	---
Iron	ppm	ASTM D5185m	>750	**112**	59	---
Chromium	ppm	ASTM D5185m	>11	**<1**	<1	---
Nickel	ppm	ASTM D5185m	>10	**0**	<1	---
Titanium	ppm	ASTM D5185m		**0**	<1	---
Silver	ppm	ASTM D5185m		**0**	0	---
Aluminum	ppm	ASTM D5185m	>21	**0**	2	---
Lead	ppm	ASTM D5185m	>49	▲ **67**	13	---
Copper	ppm	ASTM D5185m	>101	▲ **115**	93	---
Tin	ppm	ASTM D5185m	>10	**1**	<1	---
Vanadium	ppm	ASTM D5185m		**0**	0	---
Cadmium	ppm	ASTM D5185m		**0**	<1	---

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	6	**3**	1	---
Barium	ppm	ASTM D5185m	0	**2**	14	---
Molybdenum	ppm	ASTM D5185m	0	**0**	<1	---
Manganese	ppm	ASTM D5185m		**3**	2	---
Magnesium	ppm	ASTM D5185m	145	**90**	93	---
Calcium	ppm	ASTM D5185m	3570	**3222**	3534	---
Phosphorus	ppm	ASTM D5185m	1290	**1014**	1090	---
Zinc	ppm	ASTM D5185m	1640	**1130**	1257	---
Sulfur	ppm	ASTM D5185m		**3498**	4671	---

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>31	**5**	4	---
Sodium	ppm	ASTM D5185m	>51	**7**	5	---
Potassium	ppm	ASTM D5185m	>20	**0**	5	---

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	**NONE**	NONE	---
Yellow Metal	scalar	*Visual	NONE	**NONE**	NONE	---
Precipitate	scalar	*Visual	NONE	**NONE**	NONE	---
Silt	scalar	*Visual	NONE	**NONE**	NONE	---
Debris	scalar	*Visual	NONE	**NONE**	NONE	---
Sand/Dirt	scalar	*Visual	NONE	**NONE**	NONE	---
Appearance	scalar	*Visual	NORML	**NORML**	NORML	---
Odor	scalar	*Visual	NORML	**NORML**	NORML	---
Emulsified Water	scalar	*Visual	>0.1	**NEG**	NEG	---
Free Water	scalar	*Visual		**NEG**	NEG	---

OIL ANALYSIS REPORT

Non-ferrous Metals

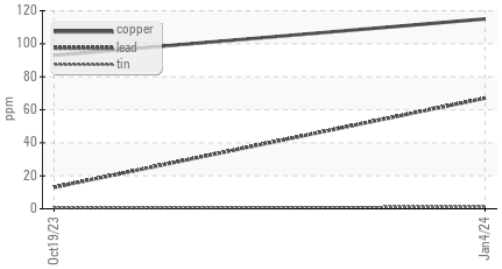

Viscosity @ 40°C

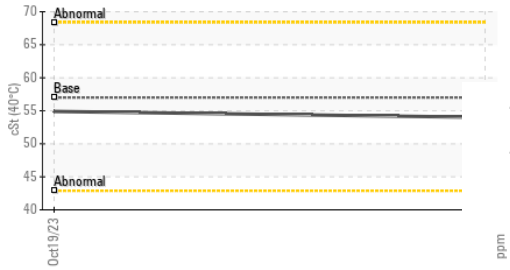

PQ

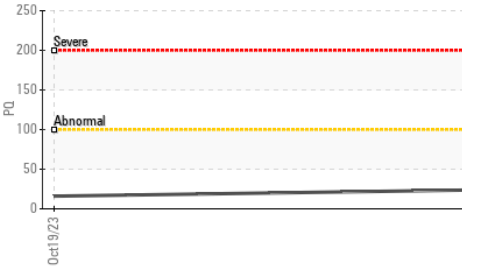

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	57.0	**54.0**	54.9	---

SAMPLE IMAGES				current	history1	history2
Color				*no image*	*no image*	*no image*
Bottom				*no image*	*no image*	*no image*

GRAPHS

Ferrous Alloys

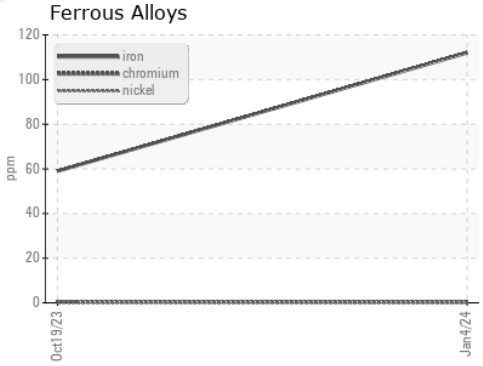

PQ

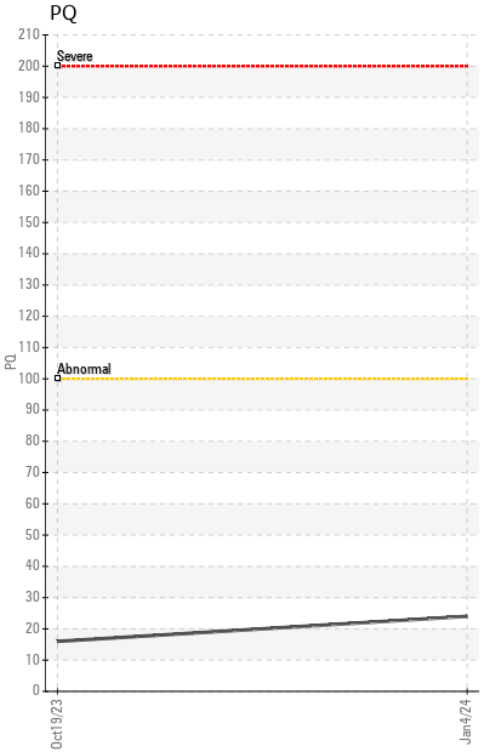

Non-ferrous Metals

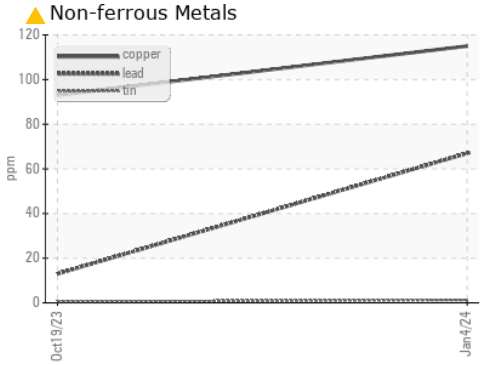

Viscosity @ 40°C

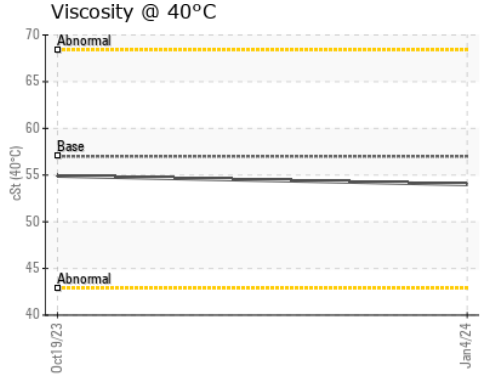

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0200283 **Recieved** : 09 Jan 2024
Lab Number : 06055578 **Diagnosed** : 10 Jan 2024
Unique Number : 10821527 **Diagnostician** : Sean Felton
Test Package : CONST (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - ASHLAND
11047 LEADBETTER RD
ASHLAND, VA
US 23005
Contact: DAVID ZIEG
dzieg@jamesriverequipment.com
T: (804)798-6001
F: (804)798-0292