STAUFF FILTRATION TECHNOLOGY

OIL ANALYSIS REPORT

Sample Rating Trend

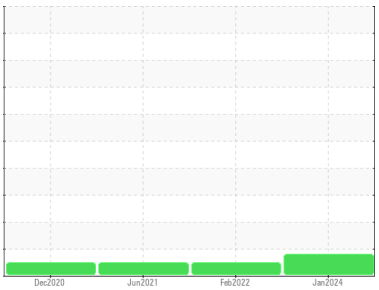

ISO

Machine Id
CHILLER PUMP 2 (S/N A738F120-2)
Component
Pump
Fluid
MOBIL DTE 26 (40 Oz)

DIAGNOSIS

▲ Recommendation
Resample at the next service interval to monitor. Due to an abnormal test result it is recommended to contact Stauff Corp at (201)-444-7800 for help resolving the issue.

Wear
All component wear rates are normal.

▲ Contamination
There is a moderate amount of silt (particulates < 14 microns in size) present in the oil.

Fluid Condition
The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number		Client Info		**ST43818**	ST36948	ST39584
Sample Date		Client Info		**08 Jan 2024**	05 Feb 2022	01 Jun 2021
Machine Age	hrs	Client Info		**0**	0	0
Oil Age	hrs	Client Info		**3700**	3100	2000
Oil Changed		Client Info		**N/A**	N/A	N/A
Sample Status				**ATTENTION**	NORMAL	NORMAL

WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>90	**<1**	<1	<1
Chromium	ppm	ASTM D5185m	>5	**<1**	0	0
Nickel	ppm	ASTM D5185m	>5	**0**	0	0
Titanium	ppm	ASTM D5185m	>3	**0**	0	0
Silver	ppm	ASTM D5185m	>3	**0**	0	<1
Aluminum	ppm	ASTM D5185m	>7	**2**	0	0
Lead	ppm	ASTM D5185m	>12	**0**	<1	0
Copper	ppm	ASTM D5185m	>30	**<1**	<1	<1
Tin	ppm	ASTM D5185m	>9	**0**	0	0
Antimony	ppm	ASTM D5185m		**---**	0	0
Vanadium	ppm	ASTM D5185m		**0**	0	0
Cadmium	ppm	ASTM D5185m		**0**	0	0

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m		**0**	0	6
Barium	ppm	ASTM D5185m		**0**	0	0
Molybdenum	ppm	ASTM D5185m		**0**	0	0
Manganese	ppm	ASTM D5185m		**0**	0	0
Magnesium	ppm	ASTM D5185m		**<1**	0	0
Calcium	ppm	ASTM D5185m		**61**	132	130
Phosphorus	ppm	ASTM D5185m		**383**	490	480
Zinc	ppm	ASTM D5185m		**536**	690	727
Sulfur	ppm	ASTM D5185m		**1392**	6918	7831

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>60	**2**	2	2
Sodium	ppm	ASTM D5185m		**0**	0	<1
Potassium	ppm	ASTM D5185m	>20	**1**	<1	0
Water	%	ASTM D6304	>.1	**0.004**	0.007	0.011
ppm Water	ppm	ASTM D6304	>1000	**47**	79.0	112.1

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>5000	▲ **5549**	820	1179
Particles >6µm		ASTM D7647	>1300	**799**	98	189
Particles >14µm		ASTM D7647	>160	**15**	6	11
Particles >21µm		ASTM D7647	>40	**4**	0	4
Particles >38µm		ASTM D7647	>10	**0**	0	0
Particles >71µm		ASTM D7647	>3	**0**	0	0
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ **20/17/11**	17/14/10	17/15/11

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045		**0.35**	0.699	0.797

STAUFF FILTRATION TECHNOLOGY

OIL ANALYSIS REPORT

Particle Trend

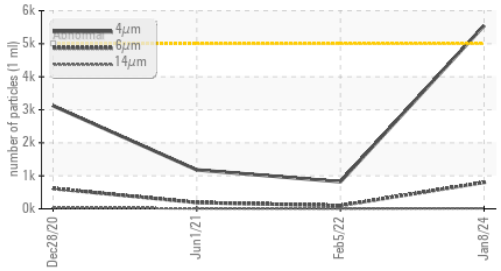

Water (KF)

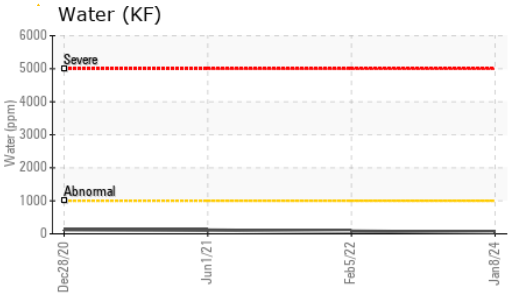

Acid Number

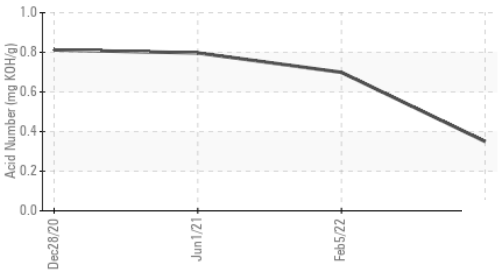

Water (KF)

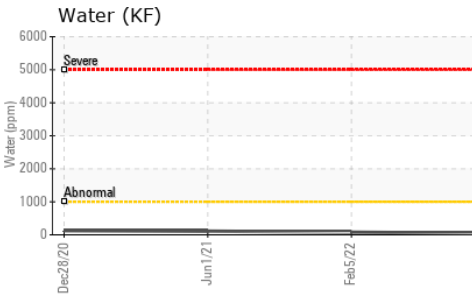

Viscosity @ 40°C

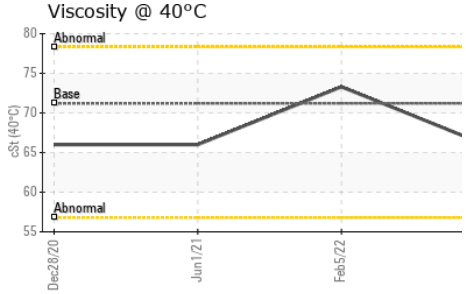

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Precipitate	scalar	*Visual	NONE	**NONE**	NONE	NONE
Silt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Debris	scalar	*Visual	NONE	**NONE**	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Appearance	scalar	*Visual	NORML	**NORML**	NORML	NORML
Odor	scalar	*Visual	NORML	**NORML**	NORML	NORML
Emulsified Water	scalar	*Visual	>.1	**NEG**	NEG	NEG
Free Water	scalar	*Visual		**NEG**	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	71.2	**66.0**	73.3	66.0

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color			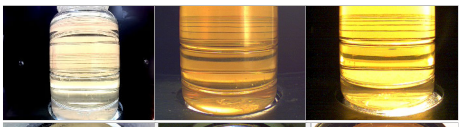		
Bottom			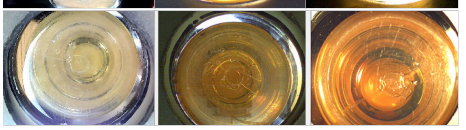		

GRAPHS

Ferrous Alloys

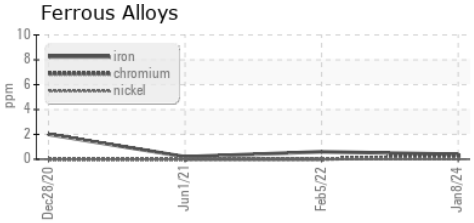

Non-ferrous Metals

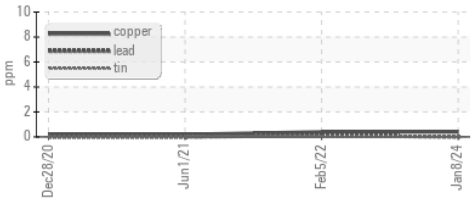

Viscosity @ 40°C

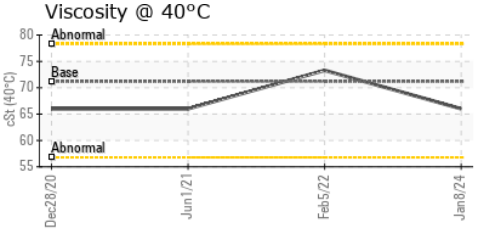

Particle Count

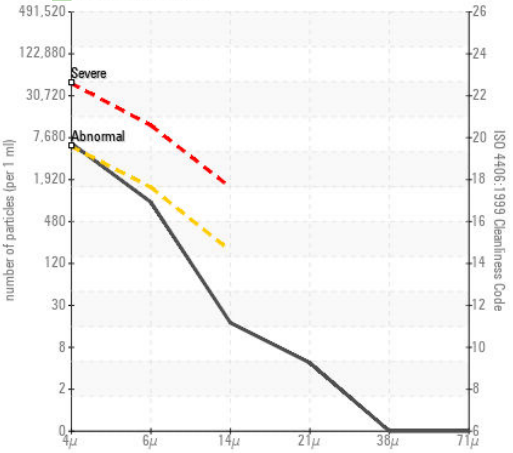

Acid Number

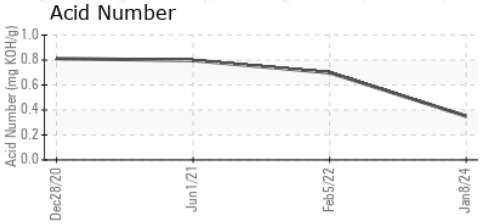

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : ST43818 **Recieved** : 12 Jan 2024
Lab Number : 06060231 **Diagnosed** : 16 Jan 2024
Unique Number : 10831613 **Diagnostician** : Don Baldridge
Test Package : IND 2 (Additional Tests: KF, PrtCount)

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

WINDSHEAR - JACOBS
1050 IVEY CLINE RD
CONCORD, NC
US 28027
Contact: SAWSON SAMIMY
sawson.samimy@jacobs.com
T: (704)920-7647
F: