




# OIL ANALYSIS REPORT

Sample Rating Trend

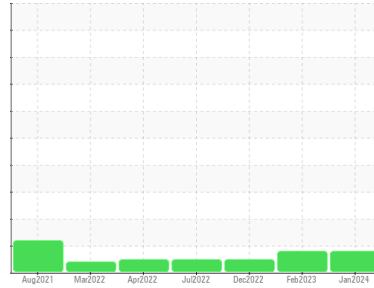

ISO



Area  
**OKLAHOMA/1052**  
Machine Id  
**45.58L [OKLAHOMA^1052]**  
Component  
**Hydraulic System**  
Fluid  
**MOBIL MOBILTRANS AST 30 (24 GAL)**

## DIAGNOSIS

### Recommendation

The filter change at the time of sampling has been noted. Resample at the next service interval to monitor.

### Wear

All component wear rates are normal.

### Contamination

There is a light amount of silt (particulates < 14 microns in size) present in the oil.

### Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>WC0857367</b>	WC0758710	WC0758787
Sample Date	Client Info		<b>08 Jan 2024</b>	14 Feb 2023	19 Dec 2022
Machine Age	hrs	Client Info	<b>7323</b>	4983	4633
Oil Age	hrs	Client Info	<b>500</b>	350	1642
Oil Changed	Client Info		<b>Not Chngd</b>	Changed	Not Chngd
Sample Status			<b>ATTENTION</b>	ATTENTION	NORMAL

## CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.1	<b>NEG</b>	NEG	NEG

## WEAR METALS

	method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185m	>20	<b>5</b>	5	8
Chromium	ppm	ASTM D5185m	>10	<b>&lt;1</b>	0	0
Nickel	ppm	ASTM D5185m	>10	<b>0</b>	0	0
Titanium	ppm	ASTM D5185m		<b>&lt;1</b>	0	0
Silver	ppm	ASTM D5185m		<b>0</b>	0	0
Aluminum	ppm	ASTM D5185m	>10	<b>1</b>	<1	2
Lead	ppm	ASTM D5185m	>10	<b>1</b>	<1	<1
Copper	ppm	ASTM D5185m	>75	<b>1</b>	0	2
Tin	ppm	ASTM D5185m	>10	<b>&lt;1</b>	0	0
Vanadium	ppm	ASTM D5185m		<b>0</b>	0	0
Cadmium	ppm	ASTM D5185m		<b>0</b>	0	0

## ADDITIVES

	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185m		<b>28</b>	14	19
Barium	ppm	ASTM D5185m		<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185m		<b>&lt;1</b>	<1	<1
Manganese	ppm	ASTM D5185m		<b>&lt;1</b>	<1	<1
Magnesium	ppm	ASTM D5185m		<b>20</b>	13	9
Calcium	ppm	ASTM D5185m		<b>2475</b>	2570	2420
Phosphorus	ppm	ASTM D5185m		<b>949</b>	892	919
Zinc	ppm	ASTM D5185m		<b>1133</b>	1101	1139
Sulfur	ppm	ASTM D5185m		<b>3932</b>	4735	4989

## CONTAMINANTS

	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185m	>20	<b>5</b>	4	2
Sodium	ppm	ASTM D5185m		<b>2</b>	<1	<1
Potassium	ppm	ASTM D5185m	>20	<b>&lt;1</b>	0	2

## FLUID CLEANLINESS

	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647		<b>20379</b>	14134	5432
Particles >6µm	ASTM D7647	>2500	<b>▲ 3178</b>	▲ 2852	308
Particles >14µm	ASTM D7647	>640	<b>121</b>	100	28
Particles >21µm	ASTM D7647	>160	<b>21</b>	16	7
Particles >38µm	ASTM D7647	>40	<b>0</b>	1	0
Particles >71µm	ASTM D7647	>10	<b>0</b>	0	0
Oil Cleanliness	ISO 4406 (c)	>--/18/16	<b>▲ 22/19/14</b>	▲ 21/19/14	20/15/12


## FLUID DEGRADATION

	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	<b>1.94</b>	0.969	0.880




# OIL ANALYSIS REPORT


▲ Particle Trend

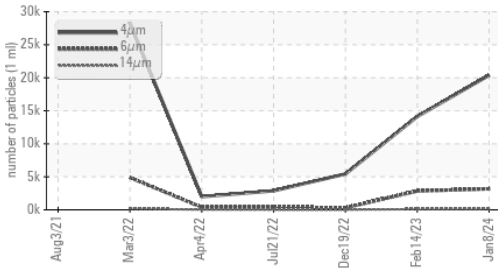


▲ Particle Trend

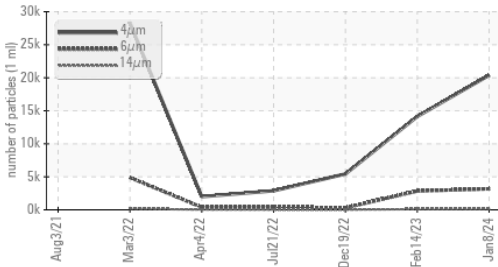

Acid Number

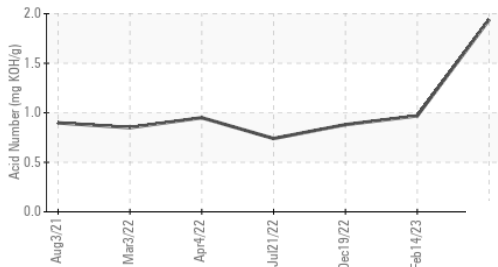


Viscosity @ 40°C

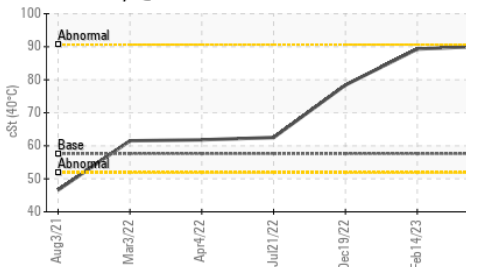

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 40°C	cSt	ASTM D445	57.6	90.2	89.3	78.4

SAMPLE IMAGES	method	limit/base	current	history1	history2
---------------	--------	------------	---------	----------	----------

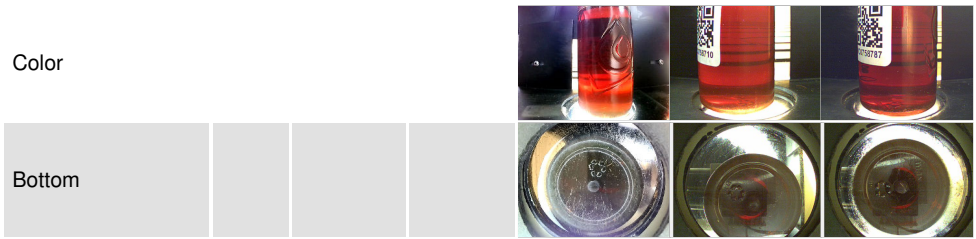


## GRAPHS


Ferrous Alloys

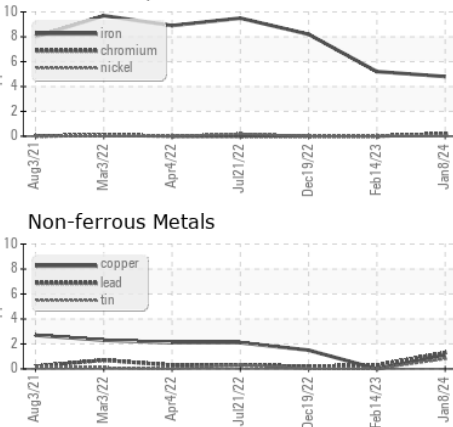


Non-ferrous Metals

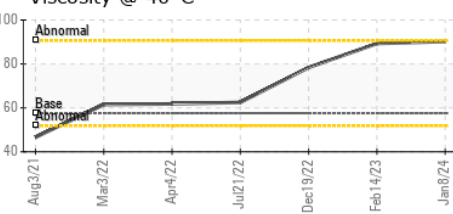


Viscosity @ 40°C

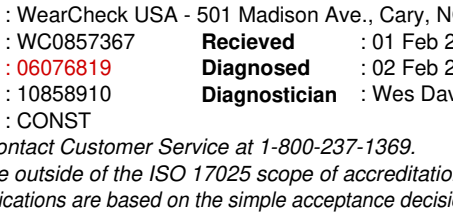

▲ Particle Count

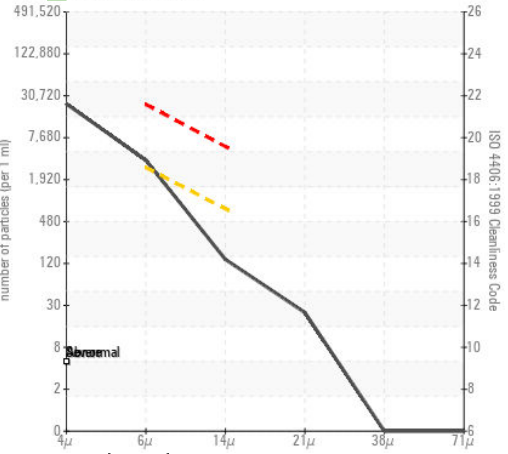

Acid Number

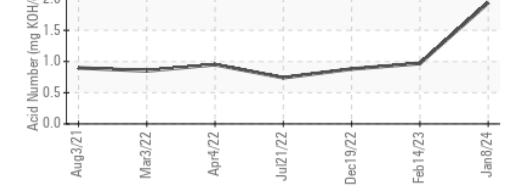

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : WC0857367  
**Lab Number** : 06076819  
**Unique Number** : 10858910  
**Test Package** : CONST

**SHERWOOD CONSTRUCTION CO INC**  
 3219 WEST MAY ST  
 WICHITA, KS  
 US 67213  
 Contact: SHAWN SOUTH  
 shawn.south@sherwood.net

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:  
F: