

OIL ANALYSIS REPORT

Sample Rating Trend

NORMAL

122201 - VOLVO L180 LOADER

Component **Diesel Engine**

PETRO CANADA DURON ADVANCED 10W

DIAGNOSIS

Recommendation Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.


Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

V30 (GAL)				Mar2024		
SAMPLE INFORM	MATION	method	limit/base	current	history1	history2
Sample Number		Client Info		SBP0005784		
Sample Date		Client Info		14 Mar 2024		
Machine Age	hrs	Client Info		4242		
Oil Age	hrs	Client Info		661		
Oil Changed		Client Info		Changed		
Sample Status				NORMAL		
CONTAMINATION	V	method	limit/base	current	history1	history2
Fuel		WC Method	>5	<1.0		
Water		WC Method	>0.2	NEG		
Glycol		WC Method		NEG		
WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>100	7		
Chromium	ppm	ASTM D5185m	>20	0		
Nickel	ppm	ASTM D5185m	>4	0		
Titanium	ppm	ASTM D5185m		0		
Silver	ppm	ASTM D5185m	>3	0		
Aluminum	ppm	ASTM D5185m	>20	2		
Lead	ppm	ASTM D5185m	>40	0		
Copper	ppm	ASTM D5185m	>330	5		
Tin	ppm	ASTM D5185m	>15	1		
Vanadium	ppm	ASTM D5185m		0		
Cadmium	ppm	ASTM D5185m		0		
ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	0	4		
Barium	ppm	ASTM D5185m	0	0		
Molybdenum	ppm	ASTM D5185m	60	56		
Manganese	ppm	ASTM D5185m	0	<1		
Magnesium	ppm	ASTM D5185m	1010	930		
Calcium	ppm	ASTM D5185m	1070	1039		
Phosphorus	ppm	ASTM D5185m	1150	1012		
Zinc	ppm	ASTM D5185m	1270	1233		
Sulfur	ppm	ASTM D5185m	2060	3473		
CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>25	5		
Sodium	ppm	ASTM D5185m		3		
Potassium	ppm	ASTM D5185m	>20	0		
INFRA-RED		method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844	>3	0.1		
Nitration	Abs/cm	*ASTM D7624	>20	7.3		
Sulfation	Abs/.1mm	*ASTM D7415	>30	18.1		
FLUID DEGRADA	TION	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414	>25	14.2		
Base Number (BN)	mg KOH/g	ASTM D2896	10.0	7.9		




OIL ANALYSIS REPORT

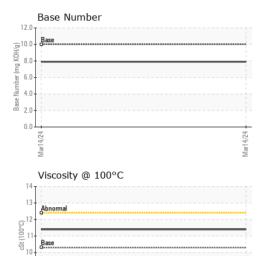



VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE		
Yellow Metal	scalar	*Visual	NONE	NONE		
Precipitate	scalar	*Visual	NONE	NONE		
Silt	scalar	*Visual	NONE	NONE		
Debris	scalar	*Visual	NONE	NONE		
Sand/Dirt	scalar	*Visual	NONE	NONE		
Appearance	scalar	*Visual	NORML	NORML		
Odor	scalar	*Visual	NORML	NORML		
Emulsified Water	scalar	*Visual	>0.2	NEG		
Free Water	scalar	*Visual		NEG		
FLUID PROPERT	TIFS	method	limit/base	current	history1	history2

FLUID PROPER	RIIES	metnoa	ilmit/base	current	nistory i	nistory2
Visc @ 100°C	cSt	ASTM D445	10.3	11.4		



Non-ferrous Metals	
copper lead	
sommer tin	
Ed. 4	
2	
Mar142.4	Mar14/24
Viscosity @ 100°C	



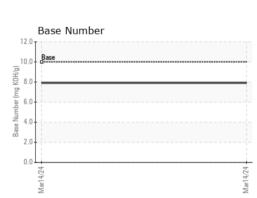



Laboratory Sample No.

: SBP0005784 Lab Number : 06124150 Unique Number : 10938301 Test Package : FLEET

To discuss this sample report, contact Customer Service at 1-800-237-1369.

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 Received : 20 Mar 2024 **Tested**

: 21 Mar 2024 Diagnosed : 21 Mar 2024 - Wes Davis Constructors Inc. - 603659

1815 Y Street Lincoln, NE US 68508

Contact: Loren Michael

LorenM@constructorslincoln.com T: (402)434-2157

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation. Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)