OIL ANALYSIS REPORT

Sample Rating Trend

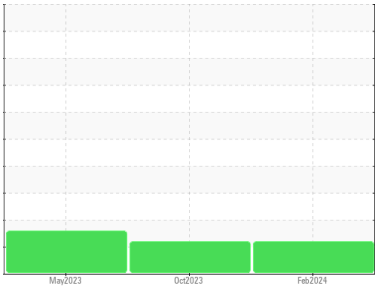

ISO

Area
PITT OHIO
Machine Id
PITT OHIO D2682
Component
Front Differential
Fluid
{not provided} (--- GAL)

DIAGNOSIS

Recommendation
No corrective action is recommended at this time. Resample at the next service interval to monitor. Please specify the brand, type, and viscosity of the oil on your next sample.

Wear
All component wear rates are normal.

Contamination
There is a high amount of silt (particulates < 14 microns in size) present in the oil.

Fluid Condition
The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number		Client Info		**WC0900848**	WC0876014	WC0828721
Sample Date		Client Info		**19 Feb 2024**	19 Oct 2023	22 May 2023
Machine Age	mls	Client Info		**101481**	51574	72
Oil Age	mls	Client Info		**0**	0	0
Oil Changed		Client Info		**N/A**	N/A	N/A
Sample Status				**ABNORMAL**	ABNORMAL	ABNORMAL

WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>500	**122**	83	9
Chromium	ppm	ASTM D5185m	>10	**<1**	<1	0
Nickel	ppm	ASTM D5185m	>10	**0**	<1	0
Titanium	ppm	ASTM D5185m		**0**	0	0
Silver	ppm	ASTM D5185m		**0**	0	0
Aluminum	ppm	ASTM D5185m	>25	**0**	<1	<1
Lead	ppm	ASTM D5185m	>25	**0**	0	0
Copper	ppm	ASTM D5185m	>100	**2**	<1	0
Tin	ppm	ASTM D5185m	>10	**<1**	0	<1
Vanadium	ppm	ASTM D5185m		**0**	0	<1
Cadmium	ppm	ASTM D5185m		**0**	0	0

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m		**91**	94	116
Barium	ppm	ASTM D5185m		**0**	0	0
Molybdenum	ppm	ASTM D5185m		**<1**	0	0
Manganese	ppm	ASTM D5185m		**8**	8	2
Magnesium	ppm	ASTM D5185m		**161**	172	181
Calcium	ppm	ASTM D5185m		**1**	2	0
Phosphorus	ppm	ASTM D5185m		**1749**	1756	1693
Zinc	ppm	ASTM D5185m		**0**	0	0
Sulfur	ppm	ASTM D5185m		**28569**	25475	25056

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>75	**35**	34	3
Sodium	ppm	ASTM D5185m		**3**	3	0
Potassium	ppm	ASTM D5185m	>20	**0**	0	0
Water	%	ASTM D6304	>.2	**0.019**	0.015	0.029
ppm Water	ppm	ASTM D6304	>2000	**191**	159	290.0

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>20000	▲ **112986**	▲ 115795	▲ 132540
Particles >6µm		ASTM D7647	>5000	● **6414**	▲ 16432	▲ 44230
Particles >14µm		ASTM D7647	>640	**267**	50	▲ 864
Particles >21µm		ASTM D7647	>160	**67**	12	128
Particles >38µm		ASTM D7647	>40	**2**	1	3
Particles >71µm		ASTM D7647	>10	**0**	0	0
Oil Cleanliness		ISO 4406 (c)	>21/19/16	▲ **24/20/15**	▲ 24/21/13	▲ 24/23/17

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045		**0.84**	0.56	0.86

OIL ANALYSIS REPORT

Particle Trend

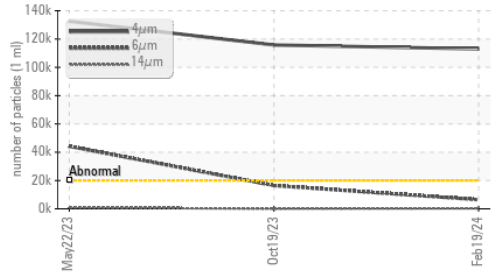

Water (KF)

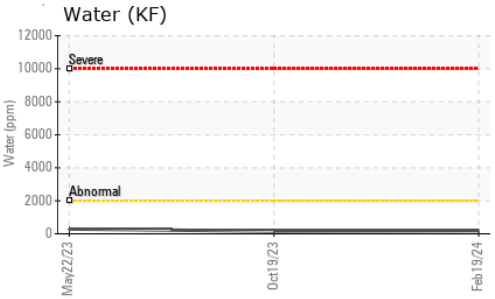

Viscosity @ 100°C

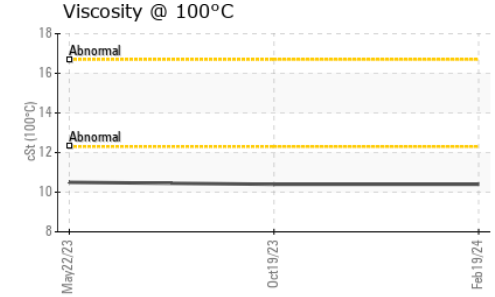

Water (KF)

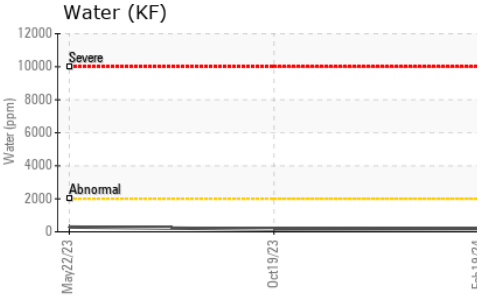

Viscosity @ 40°C

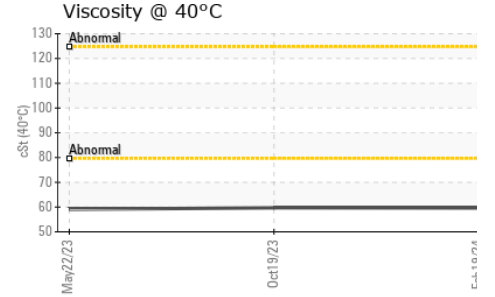

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Precipitate	scalar	*Visual	NONE	**NONE**	NONE	NONE
Silt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Debris	scalar	*Visual	NONE	**NONE**	NONE	LIGHT
Sand/Dirt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Appearance	scalar	*Visual	NORML	**NORML**	NORML	NORML
Odor	scalar	*Visual	NORML	**NORML**	NORML	NORML
Emulsified Water	scalar	*Visual	>.2	**NEG**	NEG	NEG
Free Water	scalar	*Visual		**NEG**	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445		**59.6**	59.7	59.1
Visc @ 100°C	cSt	ASTM D445		**10.4**	10.4	10.5
Viscosity Index (VI)	Scale	ASTM D2270		**164**	164	168

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color					
Bottom					

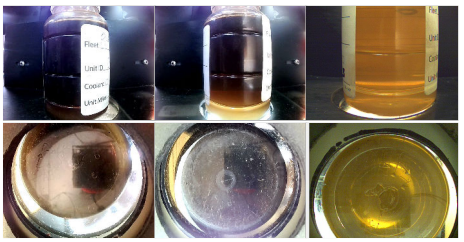

GRAPHS

Ferrous Alloys

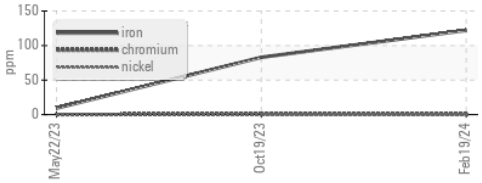

Non-ferrous Metals

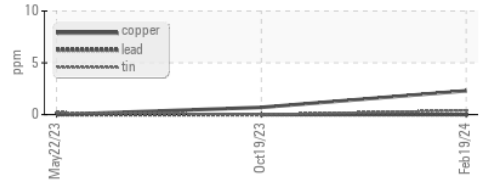

Viscosity @ 40°C

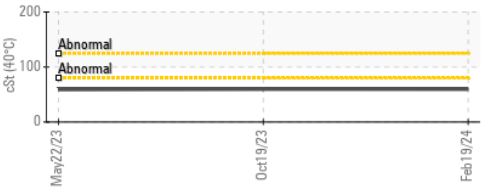

Particle Count

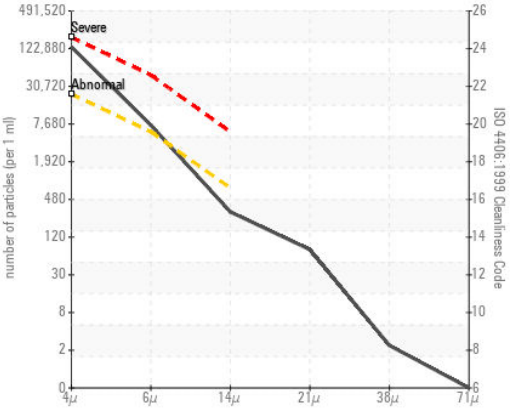

Acid Number

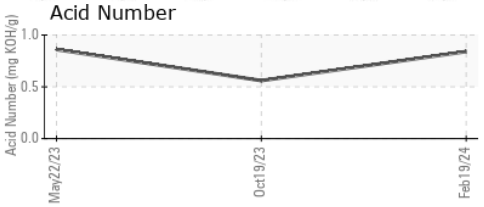

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0900848 **Received** : 21 Mar 2024
Lab Number : 06124907 **Tested** : 22 Mar 2024
Unique Number : 10939058 **Diagnosed** : 26 Mar 2024 - Jonathan Hester
Test Package : MOB 2 (Additional Tests: KF, KV100, PrtCount, VI)

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

BASF - GIANNA CREDAROLI
500 WHITE PLAINS RD
TARRYTOWN, NY
US 10591
Contact: GIANNA CREDAROLI
gianna.credaroli@basf.com
T:
F: