



OIL ANALYSIS REPORT

Sample Rating Trend



ISO



Machine Id
TOTE 68
 Component
New (Unused) Oil
 Fluid
{not provided} (--- GAL)

DIAGNOSIS

Recommendation

We advise that you filter this fluid before use.

Wear

All wear metals are normal.

Contamination

There is a high amount of silt (particulates < 14 microns in size) present in the oil.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	TLC0001654	---	---
Sample Date	Client Info	31 Mar 2024	---	---
Machine Age	hrs Client Info	0	---	---
Oil Age	hrs Client Info	0	---	---
Oil Changed	Client Info	N/A	---	---
Sample Status		ABNORMAL	---	---

WEAR METALS

method	limit/base	current	history1	history2
Iron ppm ASTM D5185m	>5	2	---	---
Chromium ppm ASTM D5185m	>5	<1	---	---
Nickel ppm ASTM D5185m	>5	<1	---	---
Titanium ppm ASTM D5185m		<1	---	---
Silver ppm ASTM D5185m	>5	<1	---	---
Aluminum ppm ASTM D5185m	>5	2	---	---
Lead ppm ASTM D5185m	>5	<1	---	---
Copper ppm ASTM D5185m	>5	<1	---	---
Tin ppm ASTM D5185m	>5	<1	---	---
Vanadium ppm ASTM D5185m		<1	---	---
Cadmium ppm ASTM D5185m		<1	---	---

ADDITIVES

method	limit/base	current	history1	history2
Boron ppm ASTM D5185m		74	---	---
Barium ppm ASTM D5185m		0	---	---
Molybdenum ppm ASTM D5185m		19	---	---
Manganese ppm ASTM D5185m		<1	---	---
Magnesium ppm ASTM D5185m		87	---	---
Calcium ppm ASTM D5185m		1130	---	---
Phosphorus ppm ASTM D5185m		510	---	---
Zinc ppm ASTM D5185m		513	---	---
Sulfur ppm ASTM D5185m		1551	---	---

CONTAMINANTS

method	limit/base	current	history1	history2
Silicon ppm ASTM D5185m	>15	5	---	---
Sodium ppm ASTM D5185m		1	---	---
Potassium ppm ASTM D5185m	>20	2	---	---
Water % ASTM D6304		NEG	---	---

FLUID CLEANLINESS






method	limit/base	current	history1	history2
Particles >4µm ASTM D7647	>5000	▲ 160909	---	---
Particles >6µm ASTM D7647	>1300	▲ 9487	---	---
Particles >14µm ASTM D7647	>160	23	---	---
Particles >21µm ASTM D7647	>40	3	---	---
Particles >38µm ASTM D7647	>10	0	---	---
Particles >71µm ASTM D7647	>3	0	---	---
Oil Cleanliness ISO 4406 (c)	>19/17/14	▲ 25/20/12	---	---

FLUID DEGRADATION

method	limit/base	current	history1	history2
Acid Number (AN) mg KOH/g ASTM D8045		1.09	---	---



OIL ANALYSIS REPORT

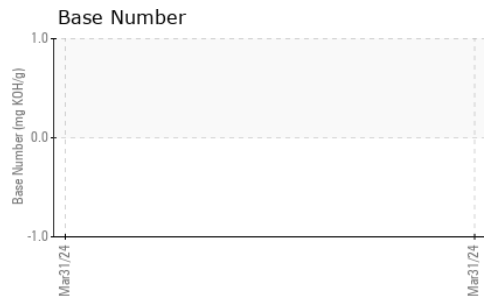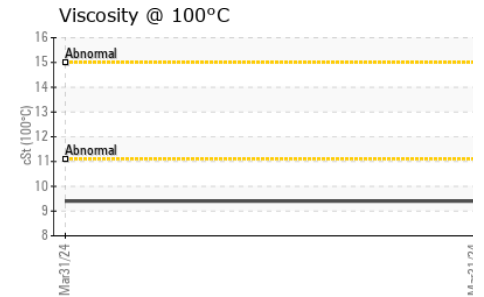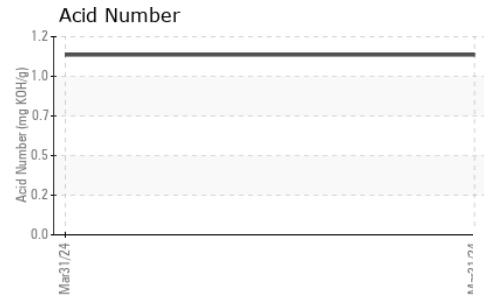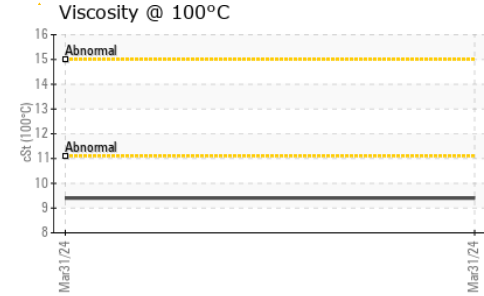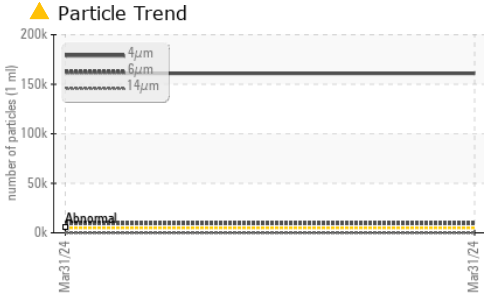




VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	---
Precipitate	scalar	*Visual	NONE	NONE	---
Silt	scalar	*Visual	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	---
Emulsified Water	scalar	*Visual	NEG	---	---
Free Water	scalar	*Visual	NEG	---	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	50.91	---	---
Visc @ 100°C	cSt	ASTM D445	9.4	---	---
Viscosity Index (VI)	Scale	ASTM D2270	170	---	---

SAMPLE IMAGES

	method	limit/base	current	history1	history2
Color				no image	no image
Bottom				no image	no image

GRAPHS

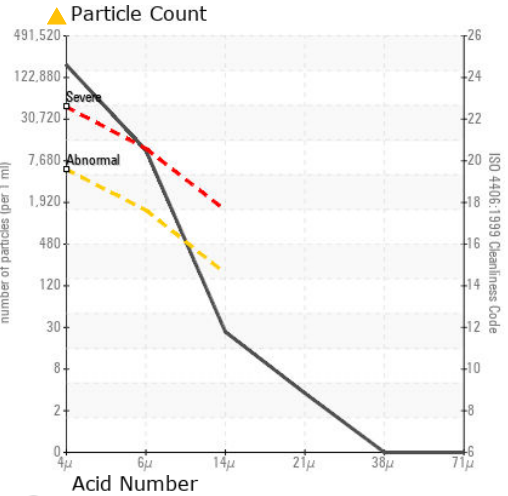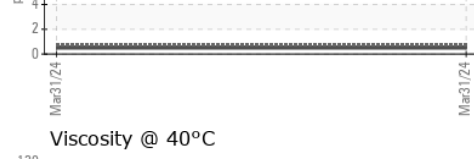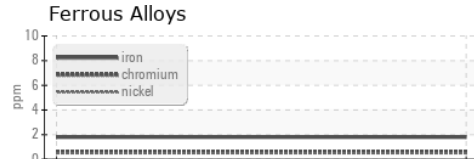

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : TLC0001654 **Received** : 29 Mar 2024
Lab Number : 06134316 **Tested** : 08 Apr 2024
Unique Number : 10953781 **Diagnosed** : 08 Apr 2024 - Doug Bogart
Test Package : PLANT (Additional Tests: FT-IR, ICP-NewOil, KV100, TBN, VI)

SUPPLY PRO
 115 EMPIRE WAY
 ATLANTA, GA
 US 30354
 Contact: MICHAEL JACKSON
 mjackson@supplypro1.com
 T: (470)991-1693
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)