




OIL ANALYSIS REPORT

Sample Rating Trend

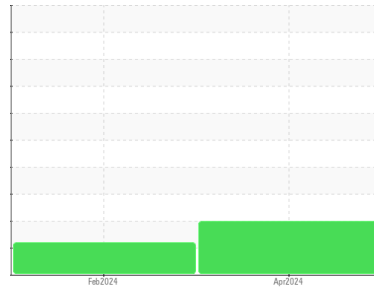

WEAR



Machine Id
27
 Component
Hydraulic System
 Fluid
HYDRO BLUE 32 (--- GAL)

DIAGNOSIS

Recommendation

We recommend you service the filters on this component if applicable. We recommend an early resample to monitor this condition.

Wear

The iron level is abnormal. All other component wear rates are normal.

Contamination

There is a high amount of silt (particulates < 14 microns in size) present in the oil.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION	method	limit/base	current	history1	history2
Sample Number	Client Info		PH0003732	PH0003736	---
Sample Date	Client Info		03 Apr 2024	22 Feb 2024	---
Machine Age	hrs	Client Info	0	0	---
Oil Age	hrs	Client Info	0	0	---
Oil Changed	Client Info		N/A	N/A	---
Sample Status			ABNORMAL	ABNORMAL	---

CONTAMINATION	method	limit/base	current	history1	history2
Water	WC Method	>0.05	NEG	NEG	---


WEAR METALS	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >20	▲ 68	2	---
Chromium	ppm	ASTM D5185m >20	0	<1	---
Nickel	ppm	ASTM D5185m >20	0	<1	---
Titanium	ppm	ASTM D5185m	0	<1	---
Silver	ppm	ASTM D5185m	0	<1	---
Aluminum	ppm	ASTM D5185m >20	0	<1	---
Lead	ppm	ASTM D5185m >20	0	<1	---
Copper	ppm	ASTM D5185m >20	0	<1	---
Tin	ppm	ASTM D5185m >20	0	<1	---
Vanadium	ppm	ASTM D5185m	0	0	---
Cadmium	ppm	ASTM D5185m	0	<1	---

ADDITIVES	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	0	4	---
Barium	ppm	ASTM D5185m	0	5	---
Molybdenum	ppm	ASTM D5185m	0	3	---
Manganese	ppm	ASTM D5185m	<1	<1	---
Magnesium	ppm	ASTM D5185m	88	15	---
Calcium	ppm	ASTM D5185m	80	42	---
Phosphorus	ppm	ASTM D5185m	352	304	---
Zinc	ppm	ASTM D5185m	401	424	---
Sulfur	ppm	ASTM D5185m	5742	2141	---

CONTAMINANTS	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >15	8	<1	---
Sodium	ppm	ASTM D5185m	2	0	---
Potassium	ppm	ASTM D5185m >20	0	<1	---






FLUID CLEANLINESS	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>10000	▲ 178617	▲ 29072	---
Particles >6µm	ASTM D7647	>2500	▲ 56993	● 4420	---
Particles >14µm	ASTM D7647	>320	40	60	---
Particles >21µm	ASTM D7647	>80	6	8	---
Particles >38µm	ASTM D7647	>20	0	0	---
Particles >71µm	ASTM D7647	>4	0	0	---
Oil Cleanliness	ISO 4406 (c)	>20/18/15	▲ 25/23/12	▲ 22/19/13	---

FLUID DEGRADATION	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	0.40	0.39	---

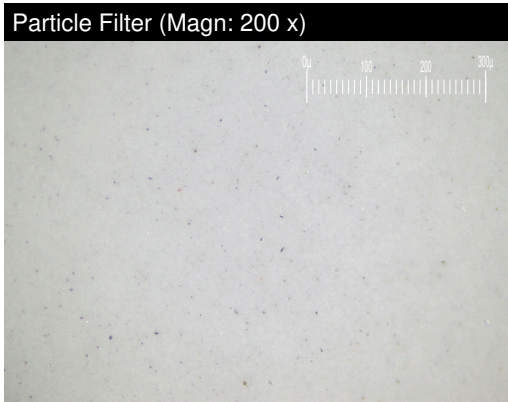




OIL ANALYSIS REPORT

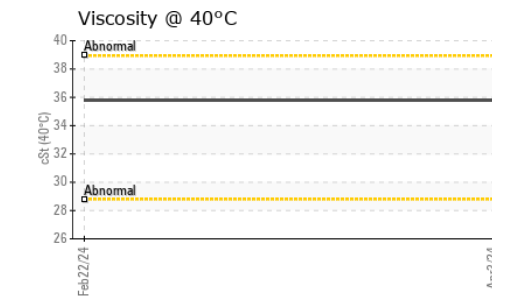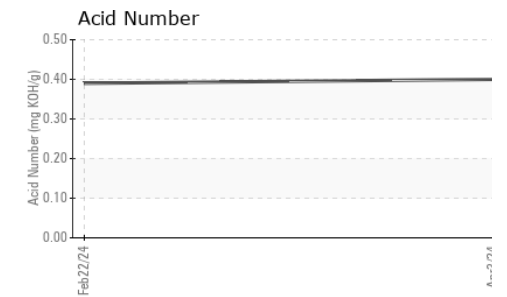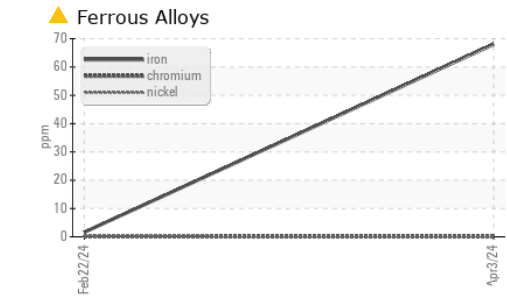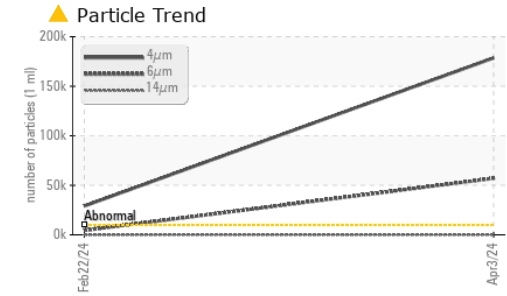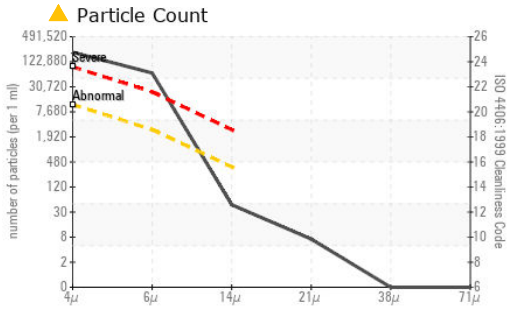






VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	---
Precipitate	scalar	*Visual	NONE	NONE	---
Silt	scalar	*Visual	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.05	NEG	---
Free Water	scalar	*Visual		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	35.8	35.8	---

SAMPLE IMAGES	method	limit/base	current	history1	history2
---------------	--------	------------	---------	----------	----------

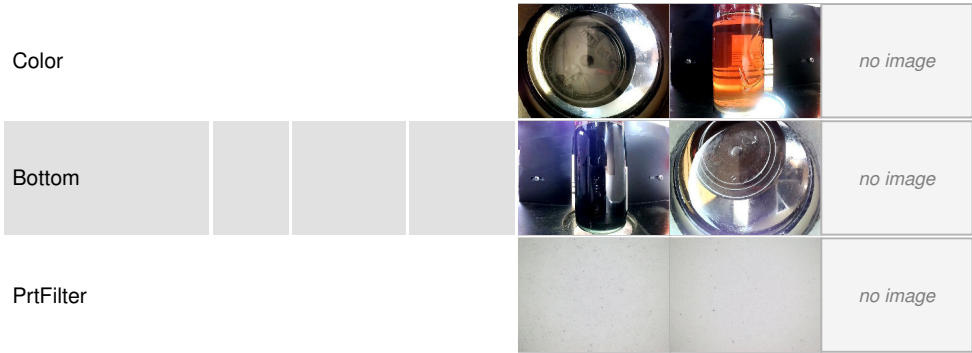

GRAPHS

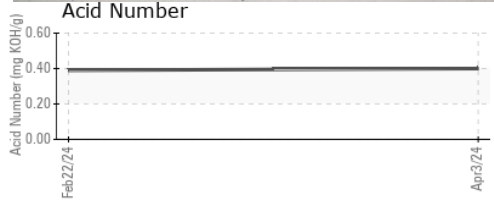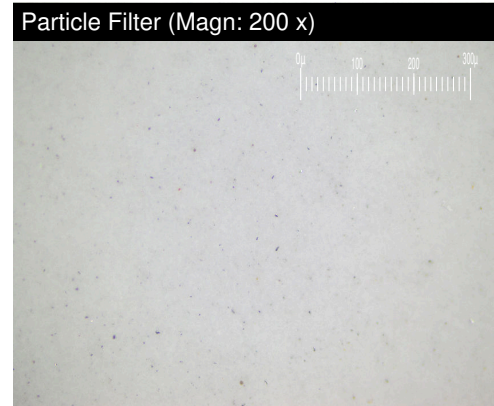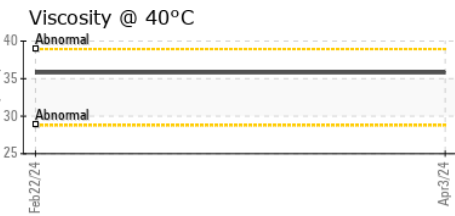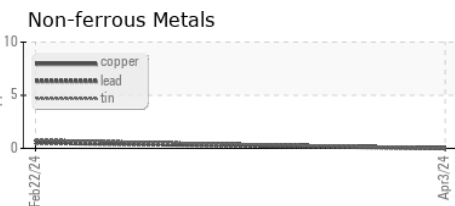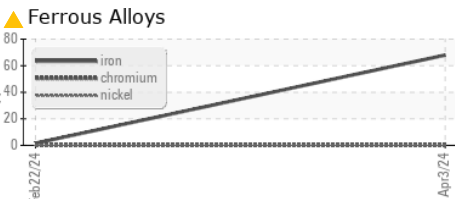

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : PH0003732 **Received** : 11 Apr 2024
Lab Number : 06145853 **Tested** : 16 Apr 2024
Unique Number : 10975931 **Diagnosed** : 16 Apr 2024 - Jonathan Hester
Test Package : PLANT (Additional Tests: PrtFilter)

ASHLAND INDUSTRIAL SERVICES
 15842 ELM DRIVE
 NEW FREEDOM, PA
 US 17349
 Contact: CHARLENE WARCHOL
 cwarchol@aisco.org

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)