


OIL ANALYSIS REPORT

Sample Rating Trend



SEDIMENT

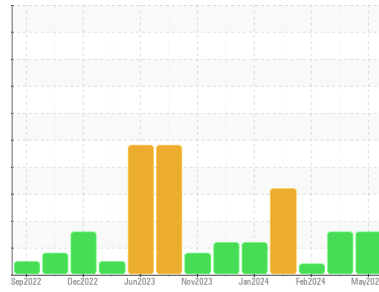

Area
Paper Cup Machines
 Machine Id
PMC 1003 POS-218 (S/N 1144378)
 Component
Circulating System
 Fluid
SUMMIT Syngear SH-1032 320 (85 GAL)

DIAGNOSIS

- Recommendation**
 We recommend you service the filters on this component. Resample at the next service interval to monitor. We were unable to perform a particle count due to a high concentration of particles present in this sample.
- Wear**
 All component wear rates are normal.
- Contamination**
 Appearance is hazy. There is a moderate amount of visible silt present in the sample.
- Fluid Condition**
 The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	TO50002254	TO50002236	TO50001914
Sample Date	Client Info	06 May 2024	09 Mar 2024	13 Feb 2024
Machine Age	hrs	0	0	0
Oil Age	hrs	0	0	0
Oil Changed	Client Info	N/A	Not Changd	Not Changd
Sample Status		ABNORMAL	ABNORMAL	ABNORMAL

WEAR METALS

method	limit/base	current	history1	history2
PQ	ASTM D8184	46	14	21
Iron	ppm	20	8	5
Chromium	ppm	<1	<1	0
Nickel	ppm	28	29	<1
Titanium	ppm	<1	<1	0
Silver	ppm	0	<1	0
Aluminum	ppm	2	<1	<1
Lead	ppm	<1	2	1
Copper	ppm	4	3	2
Tin	ppm	2	1	<1
Vanadium	ppm	<1	<1	0
Cadmium	ppm	<1	<1	0

ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm	85	78	97
Barium	ppm	0	0	0
Molybdenum	ppm	0	0	0
Manganese	ppm	<1	<1	<1
Magnesium	ppm	<1	0	2
Calcium	ppm	72	56	2
Phosphorus	ppm	483	428	480
Zinc	ppm	18	8	0
Sulfur	ppm	6859	7406	7044

CONTAMINANTS

method	limit/base	current	history1	history2
Silicon	ppm	20751	13365	9543
Sodium	ppm	0	2	1
Potassium	ppm	2	1	3
Water	%	0.016	0.011	0.012
ppm Water	ppm	160	112	123






FLUID CLEANLINESS

method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>1300	---	---
Particles >6µm	ASTM D7647	>320	---	---
Particles >14µm	ASTM D7647	>80	---	---
Particles >21µm	ASTM D7647	>20	---	---
Particles >38µm	ASTM D7647	>4	---	---
Particles >71µm	ASTM D7647	>3	---	---
Oil Cleanliness	ISO 4406 (c)	>17/15/13	---	---

FLUID DEGRADATION

method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	0.79	0.80	0.72


OIL ANALYSIS REPORT

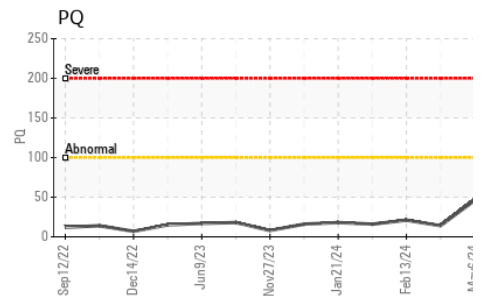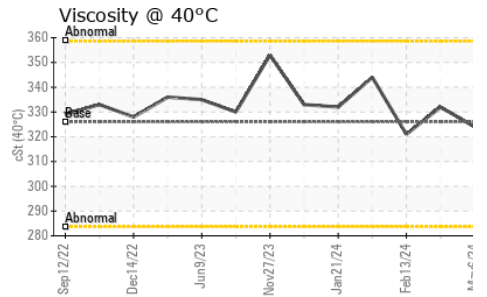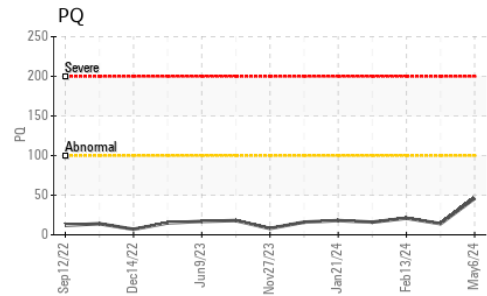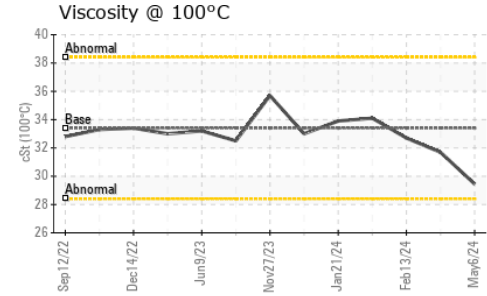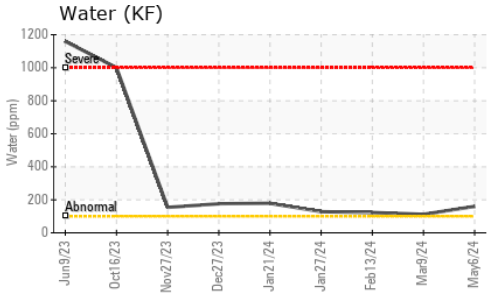





VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	▲ MODER	▲ MODER	NONE
Debris	scalar	*Visual	NONE	NONE	▲ MODER
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	● HAZY	● MILKY	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	NEG	NEG	NEG
Free Water	scalar	*Visual	NEG	NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 40°C	cSt	ASTM D445	326	324	332	321
Visc @ 100°C	cSt	ASTM D445	33.4	29.45	31.69	32.7
Viscosity Index (VI)	Scale	ASTM D2270	145	124	133	142

SAMPLE IMAGES

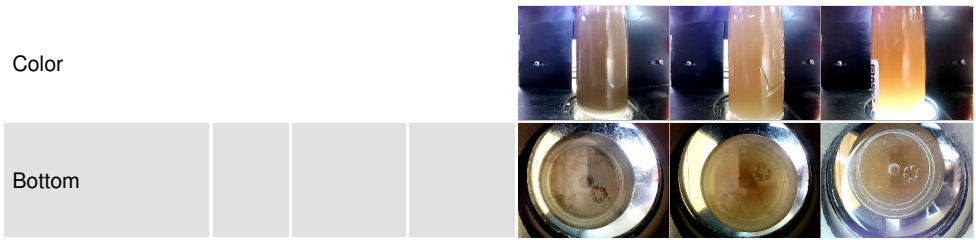

GRAPHS

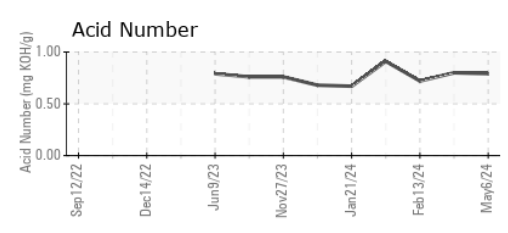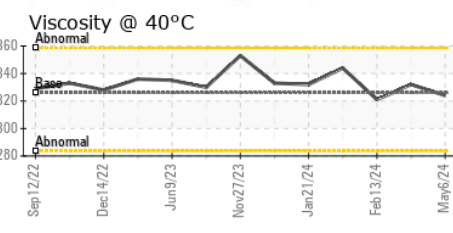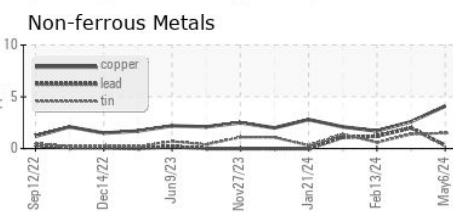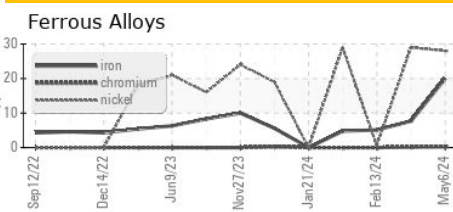

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : TO50002254 **Received** : 10 May 2024
Lab Number : 06175451 **Tested** : 16 May 2024
Unique Number : 11021504 **Diagnosed** : 16 May 2024 - Jonathan Hester
Test Package : IND 2 (Additional Tests: KF, KV100, PQ, PrtCount, VI)

DART CONTAINER CORPORATION
 4444 W LEADBETTER DR
 DALLAS, TX
 US 75236
 Contact: YON PALOMINO
 yon.palomino@dart.biz

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)