OIL ANALYSIS REPORT

Sample Rating Trend

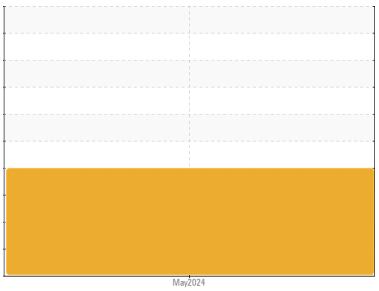

WATER

Machine Id
BRIDGEPORT 16700
Component
Blower
Fluid
{not provided} (--- GAL)

DIAGNOSIS

Recommendation
We recommend you service the filters on this component if applicable. Resample at the next service interval to monitor.

Wear
Copper and iron ppm levels are abnormal.

Contamination
There is a moderate amount of visible silt present in the sample. There is a moderate concentration of water present in the oil.

Fluid Condition
The AN level is acceptable for this fluid.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number		Client Info		**WC06176027**	---	---
Sample Date		Client Info		**09 May 2024**	---	---
Machine Age	hrs	Client Info		**0**	---	---
Oil Age	hrs	Client Info		**0**	---	---
Oil Changed		Client Info		**N/A**	---	---
Sample Status				**ABNORMAL**	---	---

WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>20	▲ **47**	---	---
Chromium	ppm	ASTM D5185m	>20	**<1**	---	---
Nickel	ppm	ASTM D5185m	>20	**1**	---	---
Titanium	ppm	ASTM D5185m		**<1**	---	---
Silver	ppm	ASTM D5185m		**0**	---	---
Aluminum	ppm	ASTM D5185m	>20	**3**	---	---
Lead	ppm	ASTM D5185m	>20	**<1**	---	---
Copper	ppm	ASTM D5185m	>20	▲ **53**	---	---
Tin	ppm	ASTM D5185m	>20	**6**	---	---
Vanadium	ppm	ASTM D5185m		**<1**	---	---
Cadmium	ppm	ASTM D5185m		**<1**	---	---

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m		**16**	---	---
Barium	ppm	ASTM D5185m		**<1**	---	---
Molybdenum	ppm	ASTM D5185m		**30**	---	---
Manganese	ppm	ASTM D5185m		**<1**	---	---
Magnesium	ppm	ASTM D5185m		**87**	---	---
Calcium	ppm	ASTM D5185m		**228**	---	---
Phosphorus	ppm	ASTM D5185m		**304**	---	---
Zinc	ppm	ASTM D5185m		**189**	---	---
Sulfur	ppm	ASTM D5185m		**4276**	---	---

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>15	**9**	---	---
Sodium	ppm	ASTM D5185m		**13**	---	---
Potassium	ppm	ASTM D5185m	>20	**4**	---	---
Water	%	ASTM D6304		▲ **0.540**	---	---
ppm Water	ppm	ASTM D6304		▲ **5400**	---	---

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045		**0.94**	---	---

OIL ANALYSIS REPORT

Water (KF)

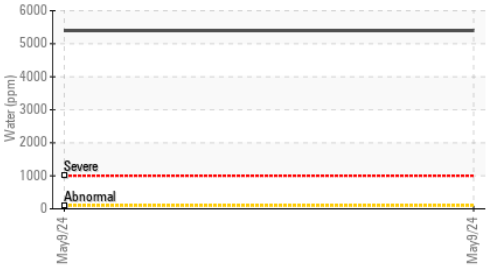

Non-ferrous Metals

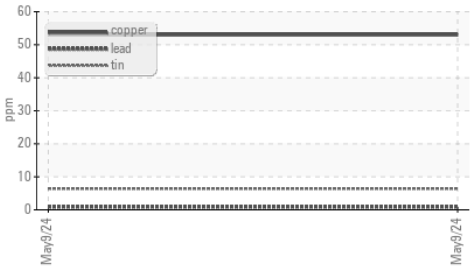

Ferrous Alloys

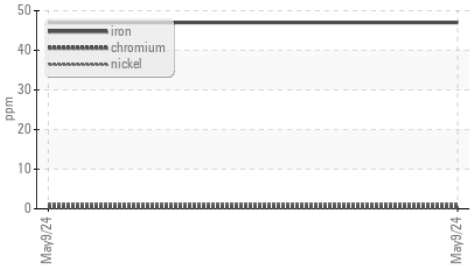

Acid Number

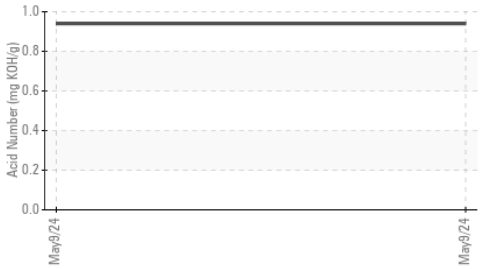

Viscosity @ 40°C

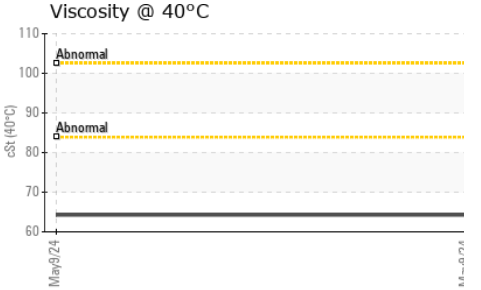

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	**NONE**	---	---
Yellow Metal	scalar	*Visual	NONE	**NONE**	---	---
Precipitate	scalar	*Visual	NONE	**NONE**	---	---
Silt	scalar	*Visual	NONE	▲ **MODER**	---	---
Debris	scalar	*Visual	NONE	**NONE**	---	---
Sand/Dirt	scalar	*Visual	NONE	**NONE**	---	---
Appearance	scalar	*Visual	NORML	**NORML**	---	---
Odor	scalar	*Visual	NORML	**NORML**	---	---
Emulsified Water	scalar	*Visual		▲ **0.2%**	---	---
Free Water	scalar	*Visual		**NEG**	---	---

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445		**64.25**	---	---

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color			*no image*	*no image*	*no image*
Bottom			*no image*	*no image*	*no image*

GRAPHS

Iron (ppm)

Lead (ppm)

Aluminum (ppm)

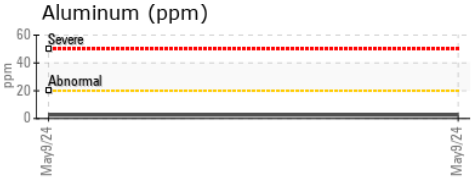

Chromium (ppm)

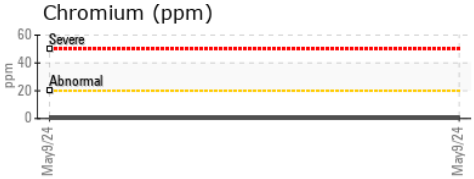

Copper (ppm)

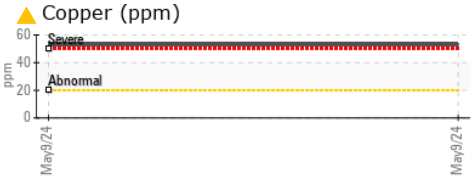

Silicon (ppm)

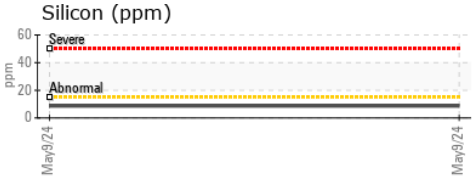

Viscosity @ 40°C

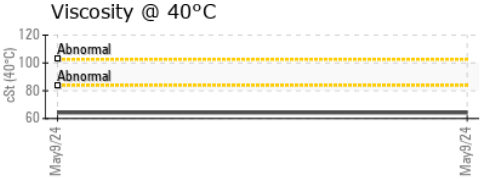

Water

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC06176027 **Received** : 10 May 2024
Lab Number : 06176027 **Tested** : 10 May 2024
Unique Number : 11022080 **Diagnosed** : 10 May 2024 - Doug Bogart
Test Package : MOB 2 (Additional Tests: KF)

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

MOMAR Incorporated
P.O. Box 19567
Atlanta, GA
US 30325
Contact: JOHN STEED
john.steed@momar.com
T: (404)355-4580
F: (678)894-4204