


OIL ANALYSIS REPORT

Sample Rating Trend



SEDIMENT

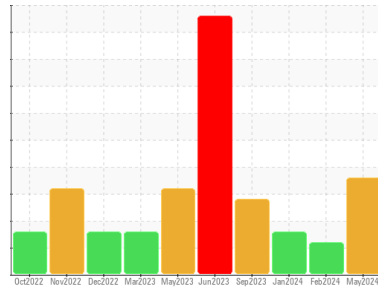

Area

Paper Cup Machines

Machine Id
PMC 1003 POS-224 (S/N 1 180443 2550 4)

Component
Circulating System

Fluid
SUMMIT Syngear SH-1032 320 (85 GAL)

DIAGNOSIS

Recommendation

We recommend you service the filters on this component. Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is a high amount of particulates present in the oil. There is a moderate amount of visible silt present in the sample.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			TO50002476	TO50001910	TO50001943
Sample Date	Client Info			07 May 2024	13 Feb 2024	11 Jan 2024
Machine Age	hrs	Client Info		0	0	0
Oil Age	hrs	Client Info		0	0	0
Oil Changed	Client Info			N/A	Not Chngd	N/A
Sample Status				ABNORMAL	ABNORMAL	ABNORMAL

WEAR METALS		method	limit/base	current	history1	history2
PQ		ASTM D8184		17	18	14
Iron	ppm	ASTM D5185m		12	10	18
Chromium	ppm	ASTM D5185m		<1	0	<1
Nickel	ppm	ASTM D5185m		0	<1	8
Titanium	ppm	ASTM D5185m		0	0	<1
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m		0	<1	2
Lead	ppm	ASTM D5185m		0	<1	0
Copper	ppm	ASTM D5185m		<1	1	2
Tin	ppm	ASTM D5185m		<1	<1	<1
Vanadium	ppm	ASTM D5185m		0	0	0
Cadmium	ppm	ASTM D5185m		0	0	0

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m		62	65	77
Barium	ppm	ASTM D5185m		<1	0	0
Molybdenum	ppm	ASTM D5185m		0	0	0
Manganese	ppm	ASTM D5185m		<1	<1	0
Magnesium	ppm	ASTM D5185m		0	2	<1
Calcium	ppm	ASTM D5185m		60	2	2
Phosphorus	ppm	ASTM D5185m		496	474	648
Zinc	ppm	ASTM D5185m		16	0	0
Sulfur	ppm	ASTM D5185m		7241	6302	8659


CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m		8199	7234	5797
Sodium	ppm	ASTM D5185m		<1	1	4
Potassium	ppm	ASTM D5185m	>20	0	3	<1
Water	%	ASTM D6304		0.017	0.012	0.015
ppm Water	ppm	ASTM D6304		175	123	155

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>1300	▲ 75538	---	---
Particles >6µm		ASTM D7647	>320	▲ 10748	---	---
Particles >14µm		ASTM D7647	>80	▲ 164	---	---
Particles >21µm		ASTM D7647	>20	▲ 24	---	---
Particles >38µm		ASTM D7647	>4	1	---	---
Particles >71µm		ASTM D7647	>3	1	---	---
Oil Cleanliness		ISO 4406 (c)	>17/15/13	▲ 23/21/15	---	---


FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045		0.72	0.70	0.69

OIL ANALYSIS REPORT


▲ Particle Trend

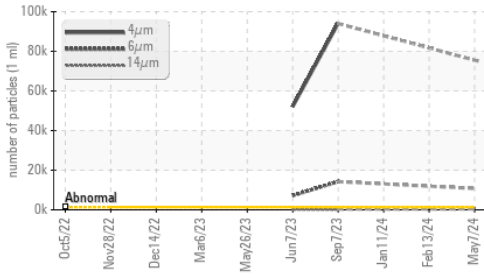


Water (KF)

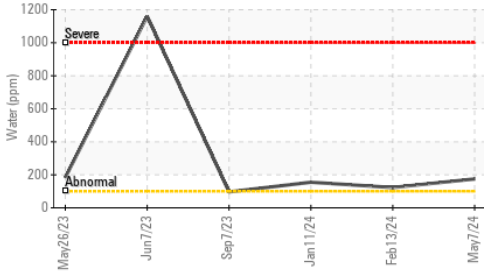


Viscosity @ 100°C

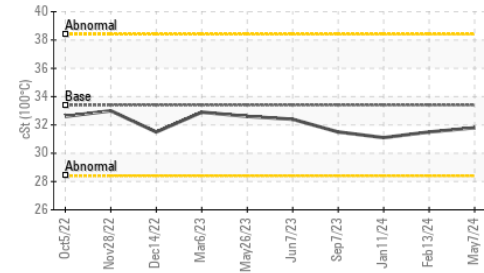

PQ

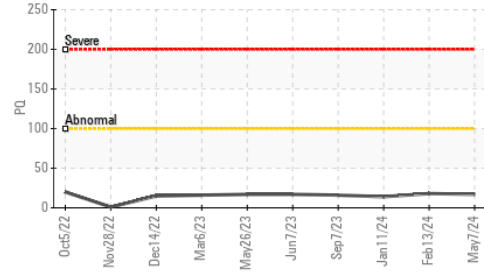


Viscosity @ 100°C

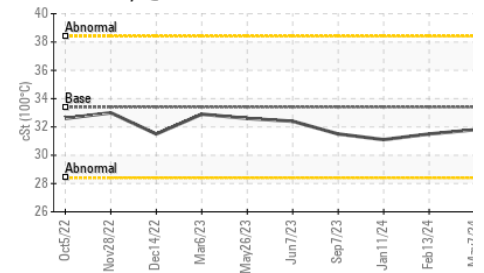

PARAMETER	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	▲ MODER	NONE	▲ MODER
Debris	scalar	*Visual	NONE	▲ MODER	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	● HAZY	● HAZY	● HAZY
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	NEG	NEG	NEG
Free Water	scalar	*Visual	NEG	NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	326	324	320
Visc @ 100°C	cSt	ASTM D445	33.4	31.5	31.1
Viscosity Index (VI)	Scale	ASTM D2270	145	135	134

SAMPLE IMAGES

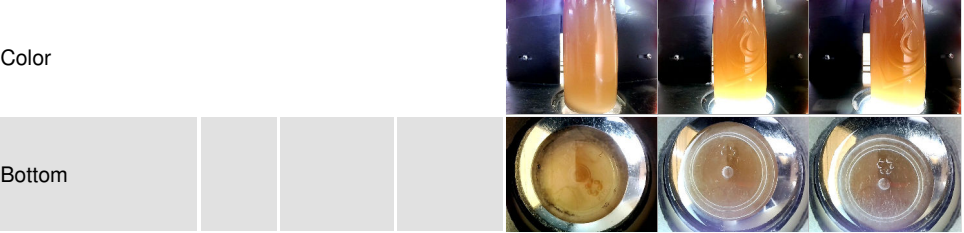


GRAPHS


Ferrous Alloys

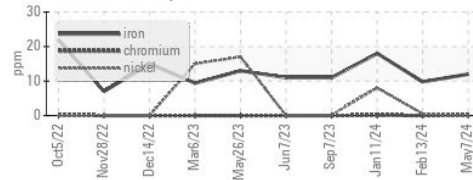


Non-ferrous Metals

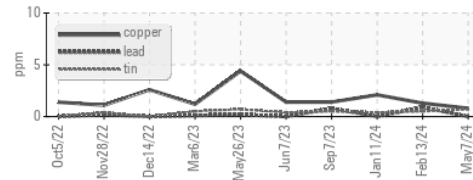


Viscosity @ 40°C

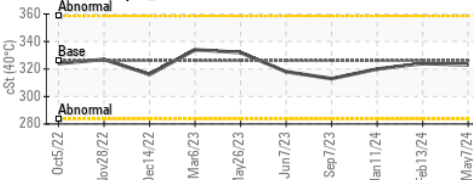

▲ Particle Count

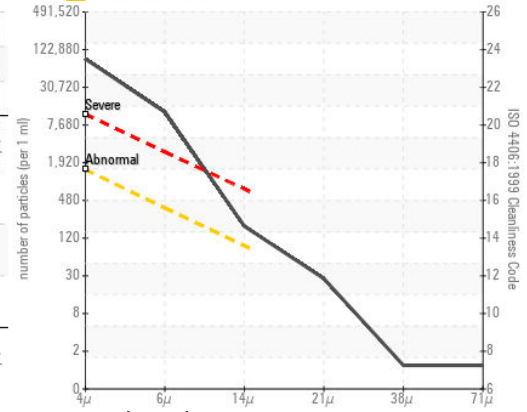

Acid Number

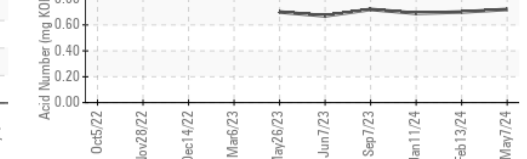

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : TO50002476 **Received** : 14 May 2024
Lab Number : 06178727 **Tested** : 15 May 2024
Unique Number : 11030053 **Diagnosed** : 16 May 2024 - Don Baldrige
Test Package : IND 2 (Additional Tests: KF, KV100, PQ, PrtCount, VI)

DART CONTAINER CORPORATION
 4444 W LEADBETTER DR
 DALLAS, TX
 US 75236
 Contact: YON PALOMINO
 yon.palomino@dart.biz
 T: (214)775-5673
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)