




PROBLEM SUMMARY



Area
OKLAHOMA/3/EG - EXCAVATOR
 Machine Id
20.69L [OKLAHOMA^3^EG - EXCAVATOR]
 Component
Right Final Drive
 Fluid
MOBIL DELVAC 1350 (--- GAL)

Sample Rating Trend

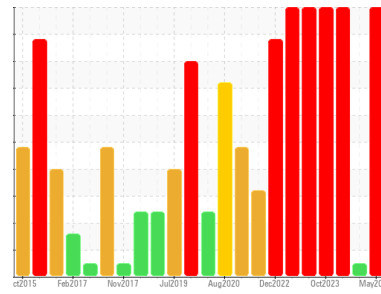


WEAR




COMPONENT CONDITION SUMMARY


▲ Non-ferrous Metals

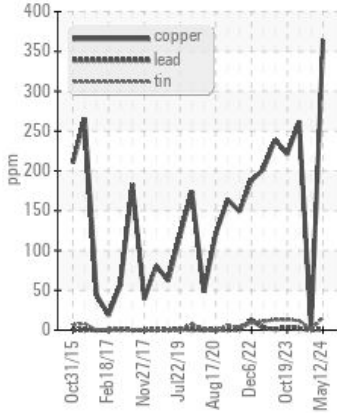


▲ Ferrous Alloys

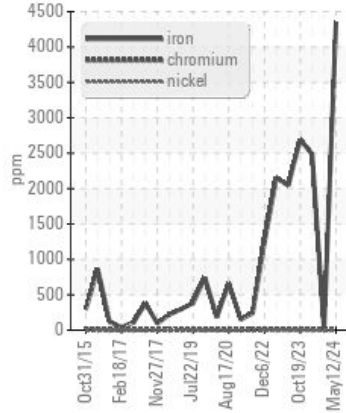

▲ Silicon (ppm)

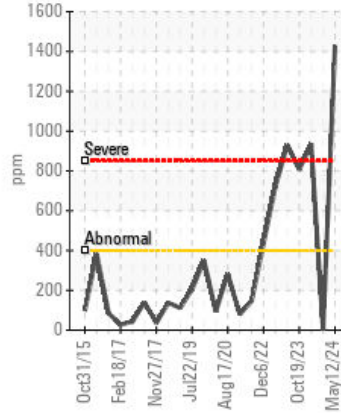

● Aluminum (ppm)

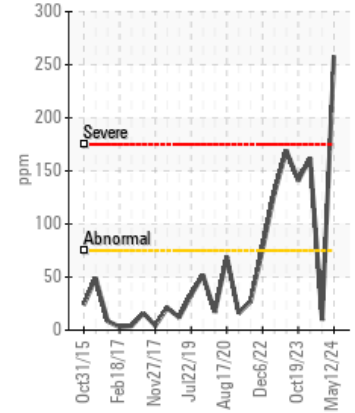

RECOMMENDATION

We advise that you check all areas where dirt can enter the system. We recommend that you drain the oil from the component if this has not already been done. We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

PROBLEMATIC TEST RESULTS

Sample Status				SEVERE	NORMAL	SEVERE
Iron	ppm	ASTM D5185m	>800	▲ 4350	5	▲ 2484
Chromium	ppm	ASTM D5185m	>10	▲ 14	1	7
Copper	ppm	ASTM D5185m	>75	▲ 364	<1	▲ 262
Tin	ppm	ASTM D5185m	>8	▲ 16	<1	▲ 12
Silicon	ppm	ASTM D5185m	>400	▲ 1427	2	▲ 936

Customer Id: SHEWIC
 Sample No.: WC0935185
 Lab Number: 06185314
 Test Package: CONST



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Don Baldrige +1
don.b505@comcast.net

To change component or sample information:
 Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Inspect Wear Source	---	---	?	We advise that you inspect for the source(s) of wear.
Change Fluid	---	---	?	We recommend that you drain the oil from the component if this has not already been done.
Resample	---	---	?	We recommend an early resample to monitor this condition.
Check Dirt Access	---	---	?	We advise that you check all areas where dirt can enter the system.

HISTORICAL DIAGNOSIS

NORMAL



13 Feb 2024 Diag: Wes Davis

Resample at the next service interval to monitor. All component wear rates are normal. There is no indication of any contamination in the oil. The condition of the oil is acceptable for the time in service.

view report



WEAR



31 Jan 2024 Diag: Don Baldrige

We advise that you check all areas where dirt can enter the system. We recommend that you drain the oil from the component if this has not already been done. We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition. Bearing and/or gear wear is indicated. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. The oil is no longer serviceable due to the presence of contaminants.

view report



WEAR



19 Oct 2023 Diag: Jonathan Hester

We advise that you check all areas where dirt can enter the system. The oil change at the time of sampling has been noted. We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition. Bearing and/or gear wear is indicated. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. The oil is no longer serviceable due to the presence of contaminants.

view report






OIL ANALYSIS REPORT



Area
OKLAHOMA/3/EG - EXCAVATOR
 Machine Id
20.69L [OKLAHOMA^3^EG - EXCAVATOR]
 Component
Right Final Drive
 Fluid
MOBIL DELVAC 1350 (--- GAL)

Sample Rating Trend

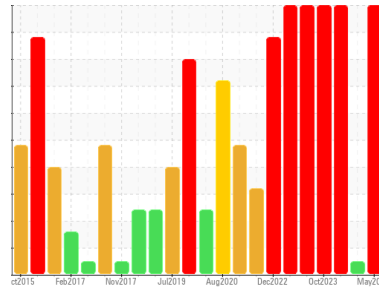

DIAGNOSIS

▲ Recommendation

We advise that you check all areas where dirt can enter the system. We recommend that you drain the oil from the component if this has not already been done. We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

▲ Wear

Bearing and/or gear wear is indicated.

▲ Contamination

Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress.

Fluid Condition

The oil is no longer serviceable due to the presence of contaminants.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		WC0935185	WC0887008	WC0886945
Sample Date	Client Info		12 May 2024	13 Feb 2024	31 Jan 2024
Machine Age	hrs	Client Info	12977	12603	12603
Oil Age	hrs	Client Info	12320	241	241
Oil Changed	Client Info		N/A	N/A	N/A
Sample Status			SEVERE	NORMAL	SEVERE

CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.2	NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >800	▲ 4350	5	▲ 2484
Chromium	ppm	ASTM D5185m >10	▲ 14	1	7
Nickel	ppm	ASTM D5185m >5	8	<1	4
Titanium	ppm	ASTM D5185m >15	19	0	11
Silver	ppm	ASTM D5185m >2	<1	0	0
Aluminum	ppm	ASTM D5185m >75	● 258	10	● 162
Lead	ppm	ASTM D5185m >10	1	0	2
Copper	ppm	ASTM D5185m >75	▲ 364	<1	▲ 262
Tin	ppm	ASTM D5185m >8	▲ 16	<1	▲ 12
Vanadium	ppm	ASTM D5185m	1	1	0
Cadmium	ppm	ASTM D5185m	<1	<1	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	15	<1	9
Barium	ppm	ASTM D5185m	0	13	<1
Molybdenum	ppm	ASTM D5185m	7	<1	3
Manganese	ppm	ASTM D5185m	35	<1	19
Magnesium	ppm	ASTM D5185m	156	<1	95
Calcium	ppm	ASTM D5185m	5826	8	3653
Phosphorus	ppm	ASTM D5185m	1532	32	938
Zinc	ppm	ASTM D5185m	1719	<1	1100
Sulfur	ppm	ASTM D5185m	18587	1151	10846

CONTAMINANTS






	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >400	▲ 1427	2	▲ 936
Sodium	ppm	ASTM D5185m	28	25	21
Potassium	ppm	ASTM D5185m >20	81	5	51

VISUAL

	method	limit/base	current	history1	history2
White Metal	scalar	*Visual NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual NONE	NONE	NONE	NONE
Precipitate	scalar	*Visual NONE	NONE	NONE	NONE
Silt	scalar	*Visual NONE	MODER	NONE	NONE
Debris	scalar	*Visual NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual NONE	NONE	NONE	NONE
Appearance	scalar	*Visual NORML	NORML	NORML	NORML
Odor	scalar	*Visual NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual >0.2	NEG	NEG	NEG
Free Water	scalar	*Visual	NEG	NEG	NEG






OIL ANALYSIS REPORT

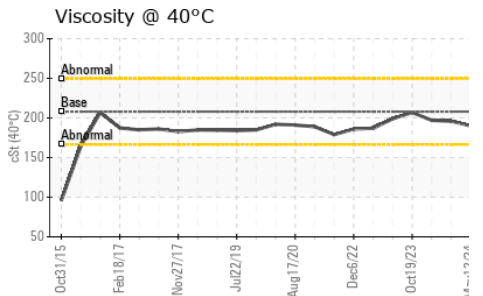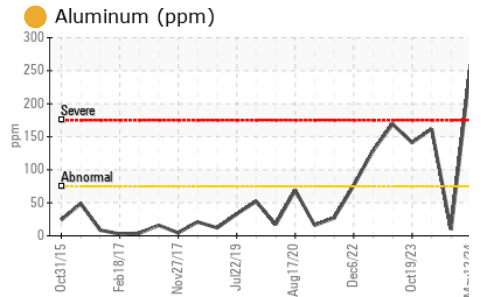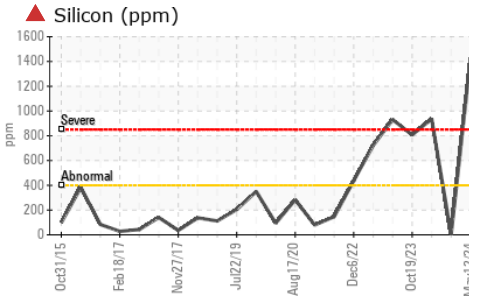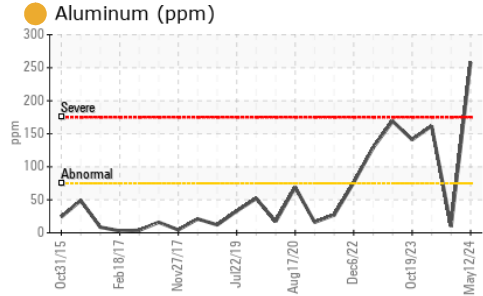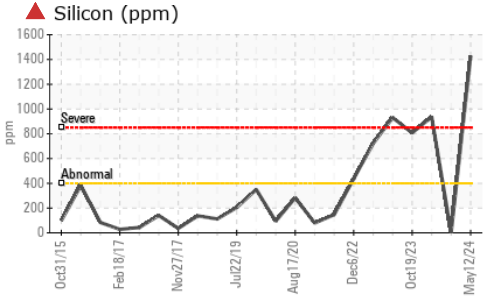

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	208	190	196	197

SAMPLE IMAGES		method	limit/base	current	history1	history2
Color				no image	no image	no image
Bottom				no image	no image	no image

GRAPHS

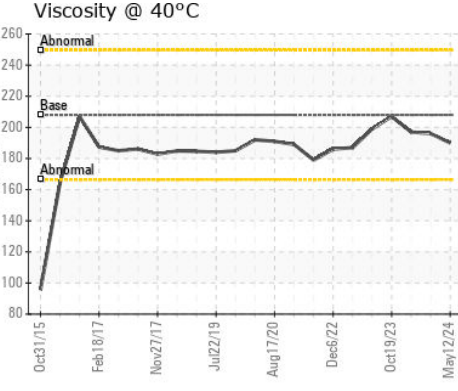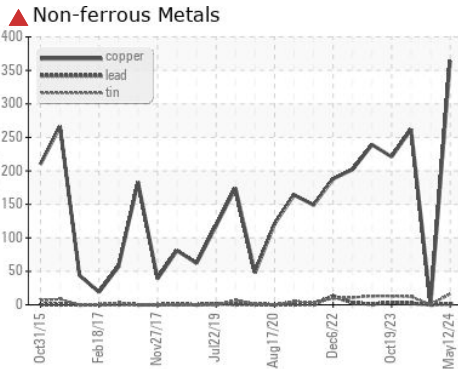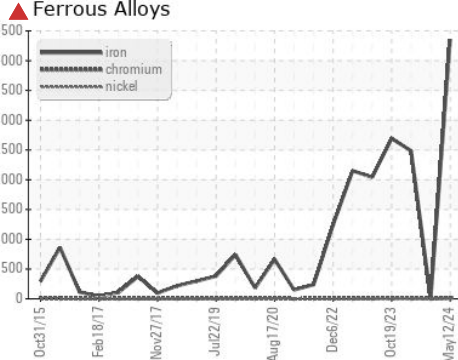

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0935185
Lab Number : **06185314**
Unique Number : 11036640
Test Package : CONST
Received : 20 May 2024
Tested : 22 May 2024
Diagnosed : 22 May 2024 - Don Baldrige

SHERWOOD CONSTRUCTION CO INC
 3219 WEST MAY ST
 WICHITA, KS
 US 67213
 Contact: DOUG KING
 doug.king@sherwood.net
 T: (316)617-3161
 F: x:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)