OIL ANALYSIS REPORT

Sample Rating Trend

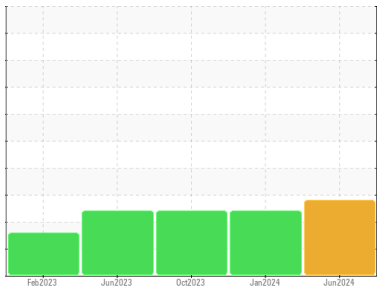

DIRT

Machine Id
BUSCH LINE 12 (S/N 5589945)
Component
Vacuum Pump
Fluid
USPI VAC 100 (--- QTS)

DIAGNOSIS

Recommendation
Resample at the next service interval to monitor.

Wear
All component wear rates are normal.

Contamination
There is a high amount of silt (particulates < 14 microns in size) present in the oil. Elemental level of silicon (Si) above normal.

Fluid Condition
The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number		Client Info		**USPM36336**	USPM30736	USPM29954
Sample Date		Client Info		**02 Jun 2024**	23 Jan 2024	09 Oct 2023
Machine Age	hrs	Client Info		**0**	0	0
Oil Age	hrs	Client Info		**0**	0	0
Oil Changed		Client Info		**N/A**	N/A	N/A
Sample Status				**ABNORMAL**	ABNORMAL	ABNORMAL

WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>20	**0**	3	2
Chromium	ppm	ASTM D5185m	>20	**0**	<1	0
Nickel	ppm	ASTM D5185m	>20	**0**	0	0
Titanium	ppm	ASTM D5185m		**0**	0	0
Silver	ppm	ASTM D5185m		**0**	0	0
Aluminum	ppm	ASTM D5185m	>20	**0**	4	0
Lead	ppm	ASTM D5185m	>20	**0**	0	0
Copper	ppm	ASTM D5185m	>20	**0**	<1	0
Tin	ppm	ASTM D5185m	>20	**0**	0	<1
Vanadium	ppm	ASTM D5185m		**0**	0	0
Cadmium	ppm	ASTM D5185m		**0**	0	0

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	0	**0**	2	4
Barium	ppm	ASTM D5185m	0	**0**	1	0
Molybdenum	ppm	ASTM D5185m	0	**0**	0	0
Manganese	ppm	ASTM D5185m		**0**	0	0
Magnesium	ppm	ASTM D5185m	0	**0**	<1	<1
Calcium	ppm	ASTM D5185m	0	**0**	<1	2
Phosphorus	ppm	ASTM D5185m	1800	**998**	983	1288
Zinc	ppm	ASTM D5185m	0	**0**	4	2
Sulfur	ppm	ASTM D5185m	0	**2**	0	29

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>15	▲ **51**	▲ 48	▲ 91
Sodium	ppm	ASTM D5185m		**3**	0	5
Potassium	ppm	ASTM D5185m	>20	**0**	<1	0
Water	%	ASTM D6304	>.1	**0.046**	0.020	0.033
ppm Water	ppm	ASTM D6304	>1000	**465**	209	336.2

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>5000	▲ **17756**	● 5595	● 7365
Particles >6µm		ASTM D7647	>1300	▲ **2624**	744	852
Particles >14µm		ASTM D7647	>160	**50**	19	25
Particles >21µm		ASTM D7647	>40	**5**	5	13
Particles >38µm		ASTM D7647	>10	**0**	1	4
Particles >71µm		ASTM D7647	>3	**0**	1	1
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ **21/19/13**	● 20/17/11	● 20/17/12

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	0.05	**0.15**	0.14	0.25

OIL ANALYSIS REPORT

Particle Trend

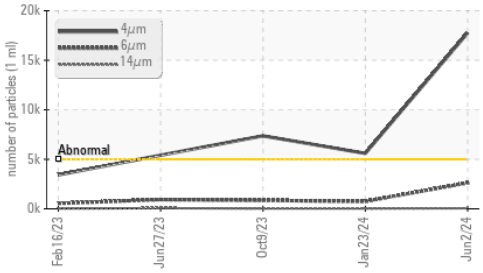

Silicon (ppm)

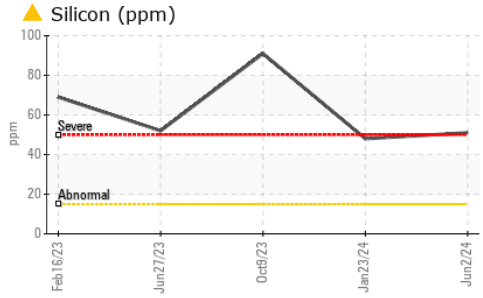

Water (KF)

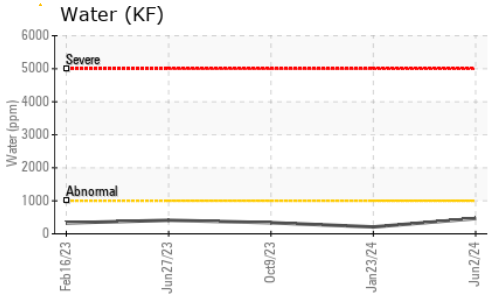

Acid Number

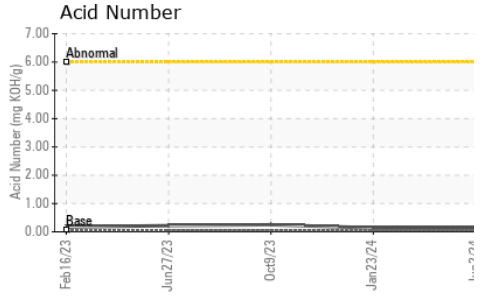

Water (KF)

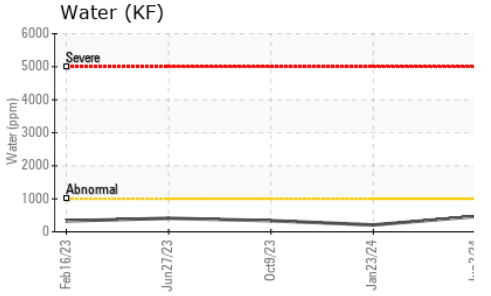

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Precipitate	scalar	*Visual	NONE	**NONE**	NONE	NONE
Silt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Debris	scalar	*Visual	NONE	**NONE**	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Appearance	scalar	*Visual	NORML	**NORML**	NORML	NORML
Odor	scalar	*Visual	NORML	**NORML**	NORML	NORML
Emulsified Water	scalar	*Visual	>.1	**NEG**	NEG	NEG
Free Water	scalar	*Visual		**NEG**	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	91	**90.1**	89.8	93.4

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color					
Bottom					

GRAPHS

Ferrous Alloys

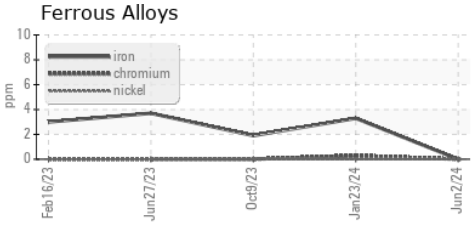

Non-ferrous Metals

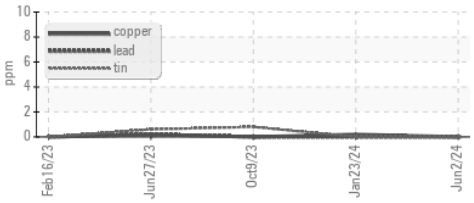

Viscosity @ 40°C

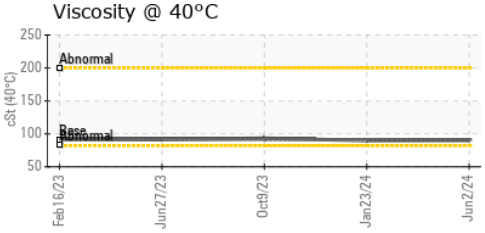

Particle Count

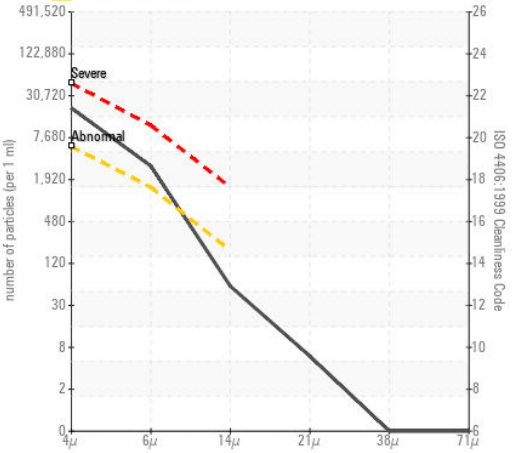

Acid Number

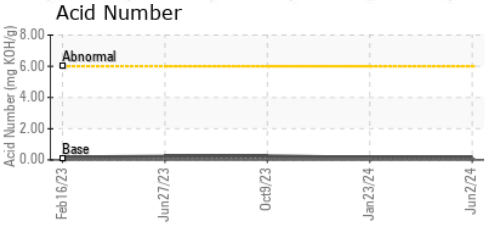

ANAB ACCREDITED ISO/IEC 17025 TESTING LABORATORY
Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : USPM36336
Lab Number : 06197674
Unique Number : 11059797
Test Package : IND 2

Received : 03 Jun 2024
Tested : 04 Jun 2024
Diagnosed : 05 Jun 2024 - Doug Bogart

ARMOUR-ECKRICH MEATS LLC - SMITHFIELD
JUNCTION CITY, KS
US 66441
Contact: SERVICE MANAGER
T:
F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)