



# OIL ANALYSIS REPORT

Sample Rating Trend



**WEAR**



Machine Id

**T-758**

Component

**Diesel Engine**

Fluid

**DIESEL ENGINE OIL SAE 15W40 (--- GAL)**

## DIAGNOSIS

### ▲ Recommendation

The oil change at the time of sampling has been noted. No corrective action is recommended at this time. We recommend an early resample to monitor this condition.

### ▲ Wear

Piston, ring and cylinder wear is indicated.

### Contamination

There is no indication of any contamination in the oil.

### Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>WC0934753</b>	---	---
Sample Date	Client Info		<b>29 Jun 2024</b>	---	---
Machine Age	mls	Client Info	<b>160458</b>	---	---
Oil Age	mls	Client Info	<b>0</b>	---	---
Oil Changed	Client Info		<b>Changed</b>	---	---
Sample Status			<b>ABNORMAL</b>	---	---

## CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<b>&lt;1.0</b>	---	---
Water	WC Method	>0.2	<b>NEG</b>	---	---

## WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>100	<b>▲ 110</b>	---
Chromium	ppm	ASTM D5185m	>20	<b>6</b>	---
Nickel	ppm	ASTM D5185m	>4	<b>1</b>	---
Titanium	ppm	ASTM D5185m		<b>&lt;1</b>	---
Silver	ppm	ASTM D5185m	>3	<b>0</b>	---
Aluminum	ppm	ASTM D5185m	>20	<b>▲ 40</b>	---
Lead	ppm	ASTM D5185m	>40	<b>&lt;1</b>	---
Copper	ppm	ASTM D5185m	>330	<b>11</b>	---
Tin	ppm	ASTM D5185m	>15	<b>1</b>	---
Vanadium	ppm	ASTM D5185m		<b>0</b>	---
Cadmium	ppm	ASTM D5185m		<b>0</b>	---

## ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	250	<b>0</b>	---
Barium	ppm	ASTM D5185m	10	<b>0</b>	---
Molybdenum	ppm	ASTM D5185m	100	<b>2</b>	---
Manganese	ppm	ASTM D5185m		<b>2</b>	---
Magnesium	ppm	ASTM D5185m	450	<b>47</b>	---
Calcium	ppm	ASTM D5185m	3000	<b>2502</b>	---
Phosphorus	ppm	ASTM D5185m	1150	<b>969</b>	---
Zinc	ppm	ASTM D5185m	1350	<b>1167</b>	---
Sulfur	ppm	ASTM D5185m	4250	<b>4127</b>	---

## CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>25	<b>8</b>	---
Sodium	ppm	ASTM D5185m	>158	<b>14</b>	---
Potassium	ppm	ASTM D5185m	>20	<b>23</b>	---
Glycol	%	*ASTM D2982		<b>NEG</b>	---

## INFRA-RED

	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844	>3	<b>1.8</b>	---
Nitration	Abs/cm	*ASTM D7624	>20	<b>12.8</b>	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	<b>32.3</b>	---


## FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414	>25	<b>22.8</b>	---
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	<b>4.1</b>	---




# OIL ANALYSIS REPORT


### ▲ Aluminum (ppm)

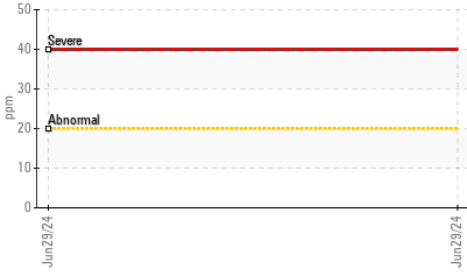


### ● FT-IR (Direct Trend)

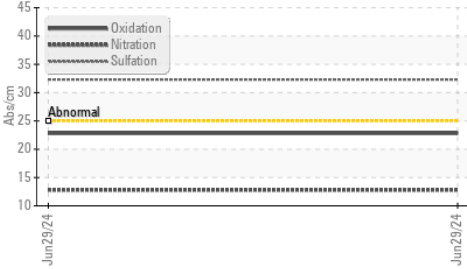

### Glycol Contamination

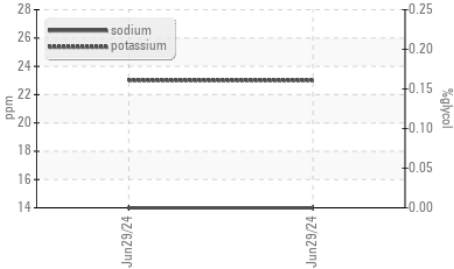

### Base Number

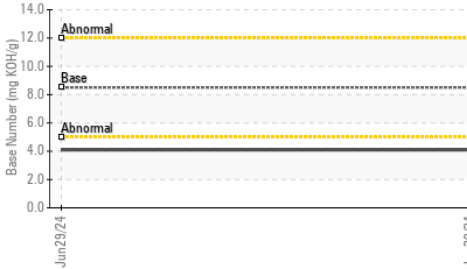

### Viscosity @ 100°C




VISUAL	method	limit/base	current	history1	history2	
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---
Precipitate	scalar	*Visual	NONE	NONE	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---	---
Free Water	scalar	*Visual		NEG	---	---


FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	14.4	15.1	---	---

### GRAPHS


### ▲ Ferrous Alloys

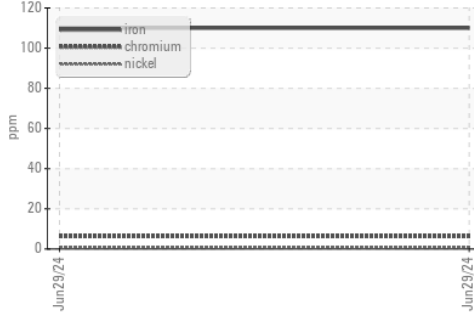


### Non-ferrous Metals

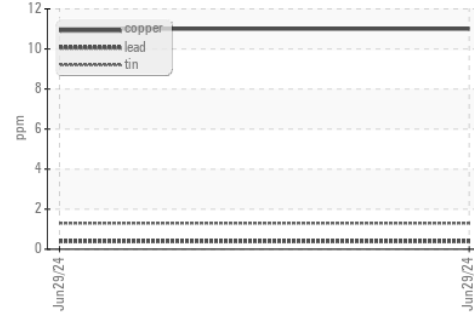

### Viscosity @ 100°C

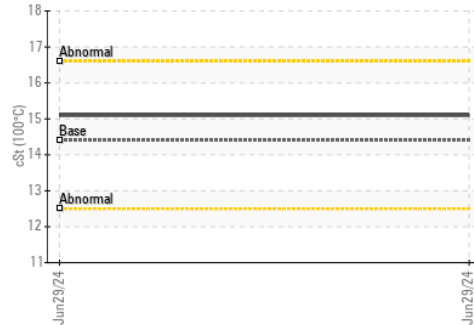

### Base Number

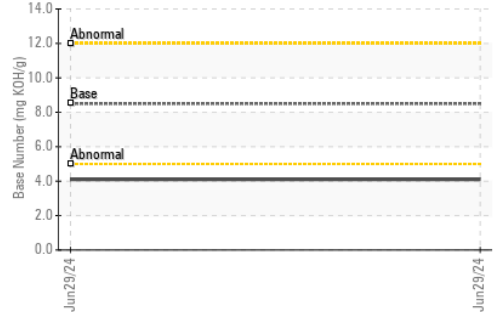

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513

**Sample No.** : WC0934753

**Lab Number** : 06237358

**Unique Number** : 11126192

**Test Package** : CONST ( Additional Tests: Glycol, TBN )

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

**Received** : 15 Jul 2024

**Tested** : 17 Jul 2024

**Diagnosed** : 17 Jul 2024 - Don Baldrige

EAI EQUIPMENT A DIV OF PLEASANT CONSTRUCTION INC

24024 FREDERICK ROAD

CLARKSBURG, MD

US 20871

Contact: Service Manager

T:

F: