




OIL ANALYSIS REPORT

Sample Rating Trend

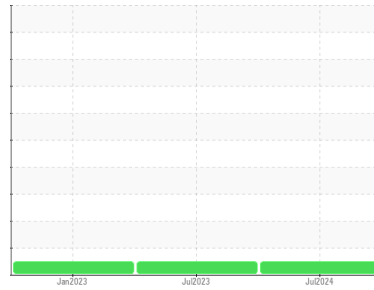

NORMAL



Area

TRUCK - URBAN

Machine Id

PETERBILT 93

Component

Diesel Engine

Fluid

SHELL Rotella T5 15W-40 (7 GAL)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			PE0004129	PE0001321	PE0000476
Sample Date	Client Info			01 Jul 2024	14 Jul 2023	11 Jan 2023
Machine Age	mls	Client Info		281670	264826	255270
Oil Age	mls	Client Info		7380	9556	6350
Oil Changed	Client Info			Changed	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

CONTAMINATION		method	limit/base	current	history1	history2
Fuel	WC Method	>5		<1.0	<1.0	<1.0
Water	WC Method	>0.2		NEG	NEG	NEG
Glycol	WC Method			NEG	NEG	NEG

WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>110	30	34	33
Chromium	ppm	ASTM D5185m	>4	<1	<1	<1
Nickel	ppm	ASTM D5185m	>2	<1	0	<1
Titanium	ppm	ASTM D5185m		59	0	0
Silver	ppm	ASTM D5185m	>2	0	0	0
Aluminum	ppm	ASTM D5185m	>25	2	2	<1
Lead	ppm	ASTM D5185m	>45	<1	0	2
Copper	ppm	ASTM D5185m	>85	1	5	5
Tin	ppm	ASTM D5185m	>4	0	<1	<1
Vanadium	ppm	ASTM D5185m		<1	0	<1
Cadmium	ppm	ASTM D5185m		<1	0	0




ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m		111	79	64
Barium	ppm	ASTM D5185m		0	<1	0
Molybdenum	ppm	ASTM D5185m		8	56	61
Manganese	ppm	ASTM D5185m		<1	<1	<1
Magnesium	ppm	ASTM D5185m		306	68	195
Calcium	ppm	ASTM D5185m		1719	2303	2071
Phosphorus	ppm	ASTM D5185m		939	1074	1017
Zinc	ppm	ASTM D5185m		1122	1317	1304
Sulfur	ppm	ASTM D5185m		3086	4403	4164

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>30	5	3	5
Sodium	ppm	ASTM D5185m		2	2	0
Potassium	ppm	ASTM D5185m	>20	4	2	2

INFRA-RED		method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844	>3	1.2	1	0.8
Nitration	Abs/cm	*ASTM D7624	>20	9.5	9.3	8.9
Sulfation	Abs/.1mm	*ASTM D7415	>30	22.8	21.0	19.3

FLUID DEGRADATION		method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414	>25	18.3	15.9	14.1
Base Number (BN)	mg KOH/g	ASTM D2896	10	7.2	6.9	7.9





OIL ANALYSIS REPORT

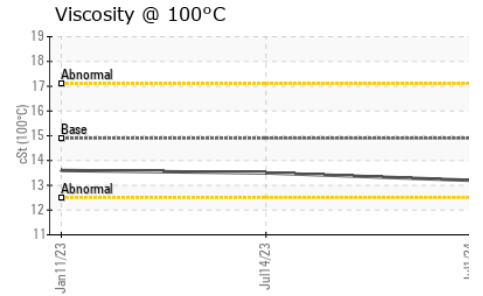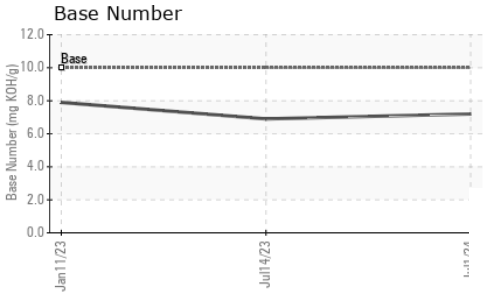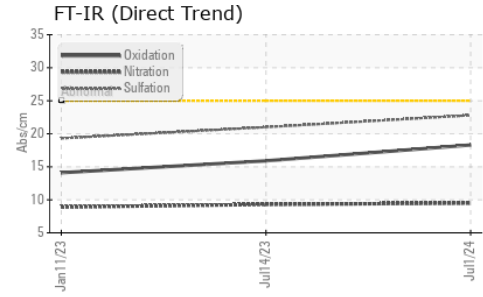

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	14.9	13.2	13.5	13.6

GRAPHS

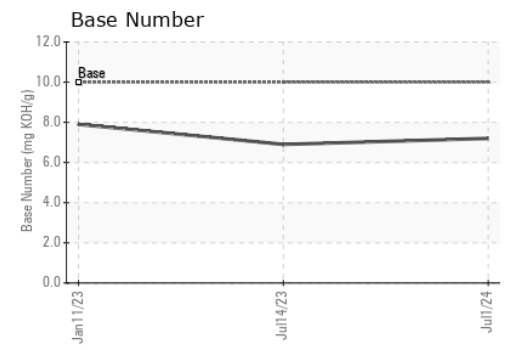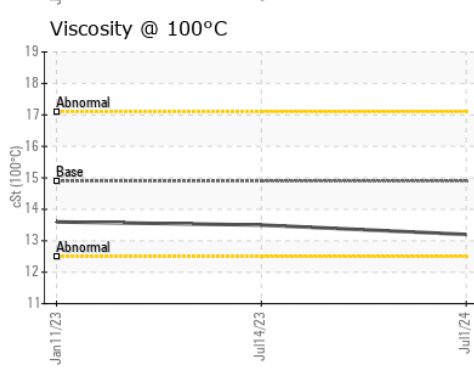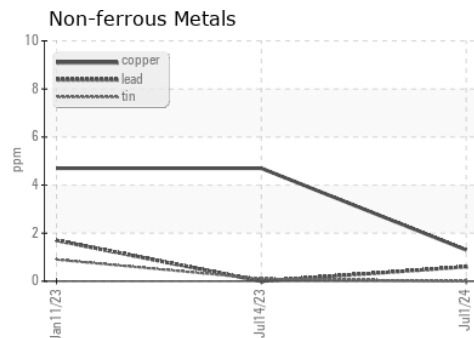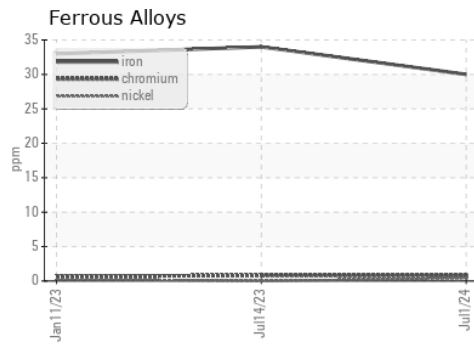

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : PE0004129 **Received** : 16 Jul 2024
Lab Number : **06238674** **Tested** : 17 Jul 2024
Unique Number : 11127508 **Diagnosed** : 18 Jul 2024 - Sean Felton
Test Package : CONST (Additional Tests: FT-IR, ICP, KV100, SCREEN, TBN)

PetroCard - Aberdeen
 110 Commerce St
 Aberdeen, WA
 US 98520
 Contact: ED ROZMARYN
 erozmaryn@petrocard.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)